arXiv:cond-mat/9911182v1 [cond-mat.str-el] 12 Nov 1999

Superconducting fluctuations and anomalous diamagnetism in underdoped $YBa_2Cu_3O_{6+x}$ from magnetization and ^{63}Cu NMR-NQR relaxation measurements

P. Carretta, A. Lascialfari, A. Rigamonti, A. Rosso and A. Varlamov *

Department of Physics "A. Volta", Unitá INFM di Pavia- Via Bassi, 6 I-27100 Pavia, ITALY

(February 7, 2008)

Abstract

Magnetization and ^{63}Cu NMR-NQR relaxation measurements are used to study the superconducting fluctuations in $YBa_2Cu_3O_{6+x}$ (YBCO) oriented powders. In optimally doped YBCO the fluctuating negative magnetization $M_{fl}(H,T)$ is rather well described by an anisotropic Ginzburg-Landau (GL) functional and the curves $M_{fl}/\sqrt{H}$ cross at T_c. In underdoped YBCO, instead, over a wide temperature range an anomalous diamagnetism is observed, stronger than in the optimally doped compound by about an order of magnitude. The field and temperature dependences of M_{fl} cannot be described either by an anisotropic GL functional or on the basis of scaling arguments. The anomalous diamagnetism is more pronounced in samples with a defined order in the Cu(1)O chains. The ^{63}Cu(2) relaxation rate shows little, if any, field dependence in the vicinity of the transition temperature $T_c(H = 0)$. It is argued how the results in the underdoped compounds can be accounted for

---

*On leave of absence from Institute of Steel and Alloys, University of Moscow

by the presence of charge inhomogeneities, favoured by chains ordering.

PACS numbers: 76.60.Es, 74.72.Bk, 74.20.Mn

Typeset using REVTEX

I. INTRODUCTION

The superconducting transition in conventional superconductors is rather well described by mean field theories, essentially because in the coherence volume ξ^3 a large number of pairs is present. On the contrary, in cuprate superconductors the small coherence length ξ, the reduced carrier density, the marked anisotropy and the high transition temperature T_c strongly enhance the superconducting fluctuations (SF). In a wide temperature range, which can extend up to 10 or 15 K above T_c, a variety of phenomena related to SF[1−3] can be detected by several experiments such as specific heat[4], thermal expansion[5], penetration depth[6], conductivity[7] and magnetization[8] measurements. Also NMR-NQR relaxation has been used to detect SF[9−13]. Recently the field dependence of the NMR relaxation rate W and of the Knight shift have been studied, by varying the magnetic field from 2 up to 24 Tesla[11,12]. Mitrovic et al.[11] attributed the field dependence of $W(H)$ to the corrections in the density of states (DOS) contribution to the spin-lattice relaxation. On the other hand, Gorny et al.[13] have observed $W(H)$ field independent, up to 14 Tesla, from 150 K to 90 K, in a sample showing a decrease in $1/T_1T$ starting around 110 K. An analysis of the role of SF in NMR experiments and of the field dependence of W has been recently carried out by Eschrig et al.[14], by extending the analitical approach of Randeria and Varlamov[15] to include short wave-length and dynamical fluctuations.

Of particular interest is the role of SF in underdoped high temperature superconductors. In fact, in these compounds one has the peculiar phenomena of the opening, at $T^* \gg T_c$, of a spin gap (as evidenced by NMR and neutron scattering) and of a pseudo-gap (as indicated by transport and ARPES experiments)[16−18]. These gaps, which are possibly connected[19], have been variously related to SF of particular character[20−22].

In this paper magnetization and ^{63}Cu(2) NMR-NQR relaxation measurements in underdoped YBCO are reported and compared with the ones in the optimally doped compound. The magnetization data yield information on the fluctuating diamagnetism (FD), while the nuclear relaxation rates W convey insights on the effects of SF on the **k**-integrated spin susceptibility in the zero frequency limit.

The paper is organized as follows. In Sect. II some basic equations describing SF and FD are recalled. After some experimental details (Sect. II), in Sect. III the experimental findings and their analysis are presented, with emphasis on the effect of the field on W and on the behavior of the diamagnetic magnetization in chain-ordered underdoped YBCO. The main results and conclusions are summarized in Sect. IV.

II. THEORETICAL FRAMEWORK AND BASIC EQUATIONS

Because of SF the number of Cooper pairs per unit volume, which is given by the average value of the square of the modulus of the order parameter $\sqrt{<|\psi|^2>}$, is different from zero above T_c. In the time-dependent Ginzburg-Landau (GL) description[2,3] the collective amplitudes and the correspondent decay times of SF are given by

$$<|\psi_{\mathbf{k}}|^2>=\frac{<|\psi_0|^2>}{1+\xi^2k^2} \quad \text{and} \quad \tau_{\mathbf{k}}=\frac{\tau_{GL}}{1+\xi^2k^2} \tag{1}$$

where $\tau_{GL}=(\pi\hbar/8k_BT_c)\epsilon^{-1}$ and $\xi(T)=\xi(0)\epsilon^{-1/2}$, with $\epsilon=(T-T_c)/T_c$. $<|\psi_{\mathbf{k}}|^2>$ plays the role of the Fourier components of the average number of pairs per unit volume, while $\tau_{\mathbf{k}}$ is the correspondent relaxation time.

Fluctuating pairs can give rise to a diamagnetic magnetization above T_c. The diamagnetic magnetization M_{fl} in general is not linear in the field H. The curves M_{fl} vs. H and M_{fl} vs. T can be tentatively analized by generalizing the Lawrence-Doniach model, using the free energy functional[23,24]

$$\begin{aligned} F[\psi]=\sum_n\int d\mathbf{r}\Big[a|\psi_n|^2+\frac{b}{2}|\psi_n|^4+ \\ +\frac{\hbar^2}{4m_{\parallel}}|[\nabla_{\parallel}-\frac{2ie}{\hbar c}\mathbf{A}_{\parallel}]\psi_n|^2+t|\psi_{n+1}-\psi_n|^2\Big] \end{aligned} \tag{2}$$

where the last term takes into account the tunneling coupling between adjacent layers. From Eq. 2, deriving the free energy in the presence of the field and by means of a numerical derivation ($M_{fl}=-\partial F/\partial H$), one can obtain the fluctuating magnetization.

According to scaling arguments[25–27] for moderate anisotropy (quasi-3D case) one expects that the magnetization curves, at constant field, cross at $T_c(H=0)$ when the magnetization is scaled by $\sqrt{H}$. The amplitude M_{fl} at $T = T_c$ departs from the Prange's result[28] by a factor $3-7$, corresponding to the anisotropy ratio $(\xi_{\parallel}/\xi_{\perp})$. Accordingly[29], the data at different fields collapse onto an universal curve when M_{fl}/T is reported as a function of $\epsilon/H^{\frac{1}{2\nu}}$, for a critical exponent for the coherence length corresponding to $\nu \simeq 0.66$.

For strong anisotropies, namely quasi-2D systems, the M_{fl} curves at constant field cross each other at $T_c(0)$. $M_{fl}(T_c)$ is larger than the value obtained from the Gaussian approximation by a factor[27] around 2. Collapse of the data onto a universal curve occurs for ν well above 0.66, usually in the range $1.2-1.4$.

The contributions to the relaxation rates W due to SF can be derived within a Fermi liquid scenario, withouth specifying the nature of the interactions[2]. The direct and most singular contribution, equivalent to the Aslamazov-Larkin paraconductivity, is not effective as nuclear relaxation mechanism. The positive Maki-Thompson (MT) contribution W_{MT} results from a purely quantum process, involving pairing of the electron with itself at a previous stage of motion, along intersecting trajectories. A negative SF contribution W_{DOS} comes from the density of states reduction when electrons are subtracted to create pairs. Approximate expressions for W_{DOS} and W_{MT} can be derived by resorting to simple physical arguments as follows. The relaxation rates can be approximated in the form

$$2W \simeq \frac{\gamma^2}{2}\langle A_{\vec{k}}\rangle k_B T \sum_{\vec{k}} \left(\frac{\chi''_{spin}(\vec{k},\omega)_{\perp}}{\omega}\right)_{\omega\to 0} \simeq \frac{\gamma^2}{2N}\langle A_{\vec{k}}\rangle k_B T \chi_{spin}(0,0)\sum_{\vec{k}} \tau_{\vec{k}} \tag{3}$$

where $< A_{\vec{k}} >$ is an average form factor for Cu nuclei and $\tau_{\vec{k}} = J_{\vec{k}}(0)$ an effective spectral density[16,30]. SF modify the static spin susceptibility $\chi_{spin}(0,0)$ and the effective correlation time $\sum_{\vec{k}} \tau_{\vec{k}}$ in Eq. 3. From Eq.1 the in-plane density of pairs is $n_c = \sum_{\vec{k}}\langle|\psi_{\vec{k}}|^2\rangle = 2n_e(k_BT_c/E_F)\ln\frac{1}{\epsilon}$ and therefore the SF imply

$$\chi_{spin}(0,0) = \frac{n_e\mu_B^2}{E_F}\left[1 - \frac{2k_BT_c}{E_F}\ln\frac{1}{\epsilon}\right] \tag{4}$$

For the dynamical part in Eq. 3, the DOS contribution can be obtained by averaging over the BZ the collective correlation time in Eq. 1:

$$\langle \tau_{DOS} \rangle = \sum_{\vec{k}} \tau_{\vec{k}}^{DOS} = \hbar\rho(E_F)\frac{\hbar}{4E_F\tau}\ln\frac{1}{\epsilon} \tag{5}$$

in the dirty limit, differing from the exact calculation[15] only by a small numerical factor. τ is the electron collision time. The MT contribution has to be evaluated in the framework of diagrammatic theories[2]. The final result corresponds to the 2D-average over the BZ of a decay rate of diffusive character $\Gamma_{\vec{k}} = Dk^2$ (with $D = {v_F}^2\tau/2$ carrier diffusion constant), phenomenologically accounting for phase breaking processes by adding in the decay rate a frequency ${\tau_\phi}^{-1}$:

$$\begin{aligned} \langle \tau_{MT} \rangle = \sum_{\vec{k}} \{(Dk^2 + \tau_\phi^{-1})\epsilon(1+\xi^2k^2)\}^{-1} = \\ = \hbar\rho(E_F)\frac{\hbar}{4E_F\tau}\frac{1}{(\epsilon-\gamma_\phi)}\ln\frac{\epsilon}{\gamma_\phi} \end{aligned} \tag{6}$$

where $\gamma_\phi = \xi^2(0)/\tau_\phi D = \pi\hbar/8K_BT_c\tau_\phi$ is a dimensionless pair breaking parameter.

By indicating with W^0 the relaxation rate in the absence of SF and by neglecting the correction to $\chi_{spin}(0,0)$ (Eq. 4), from Eqs. 3, 5 and 6 the relaxation rate in 2D systems turns out

$$W^{SF} = W^0\left[\frac{\pi\hbar}{8E_F\tau}\frac{1}{(\epsilon-\gamma_\phi)}\ln\frac{\epsilon}{\gamma_\phi} - \frac{0.8\hbar}{E_F\tau}\ln\frac{1}{\epsilon}\right] \tag{7}$$

To extend this equation to a layered system, when dimensionality crossover (2D→ 3D) occurs, one has to substitute[2] $ln(\frac{1}{\epsilon})$ by $2ln\left[2/(\sqrt{\epsilon}+\sqrt{\epsilon+r})\right]$ and $ln(\frac{\epsilon}{\gamma_\phi})$ by $2ln\left[\frac{(\sqrt{\epsilon}+\sqrt{\epsilon+r})}{(\sqrt{\gamma_\phi}+\sqrt{\gamma_\phi+r})}\right]$, with $r = 2{\xi_c}^2(0)/d^2$ anisotropy parameter (d is the interlayer distance). It is noted that the MT contribution (first term in Eq. 7) is present only for s-wave orbital pairing, while it is averaged to almost zero for d-symmetry.

III. EXPERIMENTAL DETAILS

The measurements have been carried out in oriented powders of optimally doped YBCO in one chain-disordered underdoped and in two chain-ordered underdoped YBCO samples[31] The oxygen content in the underdoped compounds was close to 6.66, with sligth differences in T_c. Electron diffraction microscopy evidenced the expected tripling of the a-axis, while resistivity measurements show a sharp transition with zero resistivity at T= 62 K and occurrence of paraconductivity below about 75 K[31]. Table I collects the main properties of the samples, as obtained from a combination of measurements.

The ^{63}Cu relaxation rates $2W \equiv {T_1}^{-1}$ have been measured by standard pulse techniques. In NQR the recovery towards the equilibrium after the saturation of the $(\pm\frac{1}{2} \rightarrow \pm\frac{3}{2})$ line is well described by an exponential law, directly yielding $6W$. For the NMR relaxation a good alignment of the $\vec{c}$ axis of the grains along the magnetic field is crucial to extract reliable values of W (H). The NMR satellite line, corresponding to the $(\frac{1}{2} \rightarrow \frac{3}{2})$ transition can be used to adjust the alignment and to monitor the spread in the orientation of the c-axis, the resonance frequency being shifted at the first order by the term $eQV_{zz}(3cos^2\theta - 1)/h$, due to the quadrupole interaction (θ angle of the $\vec{c}$-axis with the field). From the width of the spectrum (Fig. 1a) the spread in the orientation of the c-axis appears within about two degrees.

The recovery law for the NMR satellite transition is

$$y(t) = 0.5exp(-12Wt) + 0.4exp(-6Wt) + 0.1exp(-2Wt) \tag{8}$$

This law has been checked to fit well the experimental data (Fig. 1b), proving the lack of background contamination due to other resonance lines.

The magnetization has been measured by means of a Metronique Ingegnerie SQUID magnetometer, on decreasing the temperature at constant field and, at selected temperatures, by varying H. The paramagnetic contribution to M was obtained from M vs H at T $\geq$ 110 K, where practically no fluctuating magnetization is present. Then M_{fl} was derived by subtraction, singling out a small contribution from paramagnetic impurities. The paramagnetic susceptibility turns out little temperature dependent around T_c and this dependence will be neglected in discussing the much stronger diamagnetic term.

In optimally doped YBCO the measurements have been carried out at the purpose to confirm the results recently obtained in single crystals by other authors[23,27,29,32]. The isothermal magnetization curves are satisfactorily described on the basis of the anisotropic GL functional (Eq. 2), for $\epsilon \geq 4 \cdot 10^{-2}$. Only close to T_c and for $H \leq 1$ Tesla an observable departure is detected, indicating crossover to a region of non-Gaussian SF, in agreement with recent thermal expansion measurements[5]. The M_{fl} vs. T curves cross at $T_c(0)$ when M_{fl} is scaled by $\sqrt{H}$, as expected for moderate anisotropy[27].

IV. RESULTS AND ANALYSIS

Let us first comment the data in optimally doped YBCO (Fig. 2a). The comparison between the NMR and NQR W's has been already discussed in previous papers[9,10]. Here we only add a few comments motivated by more recents works[11,13,33] involving the remarkable aspect of the field dependence.

The NQR W can be compared to Eq. 7, by using the values[2] $\tau = 10^{-14}s$, $\tau_\phi = 2.10^{-13}s$ and a dephasing time parameter $\gamma_\phi = 0.2$. A quantitative fitting is inhibited by the fact that the background contribution to W does not follow the Korringa law, in view of correlation effects among carriers[16]. A firm deduction, however, is that an anisotropy parameter $r \neq 0$, and namely a crossover to a 3D regime, is required to avoid unrealistic values (2D line in Figure 2a), as indicated also by magnetization measurements (see later on).

Mitrovic et al.[11] have discussed the field dependence of T_1 in terms of quenching of the DOS term only, by resorting to the theory of Eschrig et al.[14]. The field dependence of the SF contribution to the relaxation rate is a delicate issue, because of the nontrivial interplay of many parameters which include reduced temperature ϵ, reduced field $\beta = \frac{2H}{H_{c2}}$, anisotropy parameter r, elastic and phase breaking times τ and τ_ϕ. Eschrig et al.[14] have extended the analitical approach[15] by taking into account arbitrary values of $(K_B T \tau / \hbar)$, short-wave fluctuations and dynamical fluctuations. The price of this generalization is the restriction to a 2D spectrum of SF fluctuations. In view of our experimental findings the analysis of the field effect in a purely 2D framework is questionable. On the other hand, a re-examination of the field effect for a layered system is now possible by applying the method of the DOS term regularization devised by Budzin and Varlamov[33], which has indicated how the divergences can be treated. Since the dynamical fluctuations could be relevant only for fields of the order of H_{c2}, up to $20-30$ $Tesla$ the fluctuations can be safely treated in the nearly static limit. The field dependence for weak fields ($\beta \ll \epsilon$) turns out[34]

$$W(\beta \ll \epsilon) - W(0,\epsilon) = W^{(0)} \frac{\hbar}{24 E_F \tau} \left(\kappa(T\tau) - \frac{\pi}{8\gamma_\phi} \right) \frac{\epsilon + r/2}{[\epsilon(\epsilon + r)]^{3/2}} \beta^2 \tag{9}$$

where

$$\kappa(T\tau) = \frac{7\zeta(3)}{\pi} \frac{1}{4\pi T\tau[\psi(1/2) - \psi(1/2 + 1/4\pi T\tau)] + \psi'(1/2)} = \begin{cases} 14\zeta(3)/\pi^3, & T\tau \ll 1 \\ 4T\tau \ , & 1 \ll T\tau \ll 1/\sqrt{\epsilon} \end{cases}$$

(here $\hbar = k_B = 1$).

So both effects of increase and of decrease of W on increasing the magnetic field are possible, depending on the mean free path in the specific sample. If $T\tau \lesssim 0.1$ the main correction to W is due to the MT term and one should observe W decreasing with increasing field, while if $T\tau \gtrsim 0.1$ the DOS correction becomes dominant and W is expected to increase.

As it appears from Fig. 2 the effect of the field for $T \geq T_c(H = 0)$ is small, if any. It is noted that if Eq. 7 is applied to the underdoped compounds the reduction in the Fermi energy E_F and the increase in the anisotropy (i.e. decrease of r) would imply a sizeable increase in W^{SF}. This enhancement in the underdoped compounds does not occur (see Fig. 2b and 2c for the chain-disordered and chain-ordered YBCO's, respectively), unless the decrease of W over a wide temperature range, usually related to the spin-gap opening[16], should be attributed to a field-independent DOS term. On the other hand, the conventional SF of GL character should occur only close to T_c, where, on the contrary, $\chi_{spin}(0,0)$ is little temperature dependent. Eq. 9, in principle, does predict a field dependence. However, if typical values $E_F \simeq 3000$ K, $\tau \simeq 10^{-14}$, $(\kappa(T\tau) - (\pi/8\gamma_\phi) \simeq 1$ and $r \simeq 0.1$ are used, for $\epsilon \simeq 3 \times 10^{-2}$ one has $W(\beta) - W(0) \simeq 0.15 W^{(0)} \beta^2$, hardly to evidence for $\beta \ll 1$. A comprehensive discussion of the field dependence of the SF contribution to the relaxation rate is given elsewhere[34]. Here we only remark that the results in strong fields ($\beta \gtrsim 0.2$) from Mitrovic et al.[11] can hardly be justified on the basis of Eq. 9.

As regards the magnetization measurements in optimally doped YBCO, as already mentioned, our data indicate a 3D regime crossing from Gaussian to critical fluctuations close to T_c. The value of $\gamma_{an} m_3(\infty)^{27}$ at the crossing point of the curves $M_{fl}/\sqrt{H}$ vs. T turns out around -1.5, corresponding to an anisotropy factor $\gamma_{an} = 4.5$. A collapse onto a common function is obtained when $M_{fl}/\sqrt{H}T$ is plotted as a function of $\epsilon/H^{0.747}$. The collapse fails in magnetic fields less than about 0.3 Tesla. A small-field departure from the universal function has been already observed in underdoped compounds[29], but no mention about it is found in the literature for optimally doped YBCO.

In the underdoped compounds a marked enhancement of the fluctuating magnetization is observed (Figs. 3 and 4). In Fig. 4 the susceptibilty, defined as $\frac{M}{H}$ for $H = 0.02$ Tesla, is reported. The inset is a blow up of the results around the temperature where reversing of the sign of the magnetization occurs. The susceptibilities for chain-ordered and chain-disordered underdoped samples are compared with the one in optimally doped YBCO in Fig. 5.

In underdoped YBCO the magnetization curves dramatically depart from the ones expected on the basis of Eq. 2 and numerical derivative. No crossing point is observed in the curves M_{fl} vs T and no collapse is found on anisotropic 3D or 2D-like curves for $M_{fl}/\sqrt{H}$ or M_{fl} vs $\epsilon/H^{1/2\nu}$ (Fig. 6). These anomalies are more manifested in the chain ordered compound, as it can be realized from the peculiar shape of the isothermal magnetization vs. H (Fig. 7). One could remark that a fraction of a few percent of non-percolating local superconducting regions can account for the absolute value of the diamagnetic susceptibility and for the shape of the magnetization curves. A trivial chemical inhomogeneity could be suspected. The fact that the anomalous diamagnetism has been observed in three samples differently prepared and since it is strongly enhanced in the chain-ordered ones, supports the intrinsic origin of the phenomenon. Recent theories[35,36] have discussed how a distribution of local superconducting temperatures, related to charge inhomogeneities, can cause anomalous diamagnetic effects.

Mesoscopic charge inhomogeneities have been predicted on the basis of various theoretical approaches[21,38]. In underdoped compounds one could expect the occurrence of preformed

Cooper pairs causing "local" superconductivity lacking of long-range phase coherence. An inhomogeneous distribution of carriers, on a mesoscopic scale, is supported by *ab* plane optical conductivity[37] and it is the basic ingredient of the stripes model[39]. Since the anomalous diamagnetism is enhanced in chain-ordered underdoped YBCO one is tempted to relate it to the presence of stripes. The insurgence of phase coherence among adjacent charge-rich regions can qualitatively be expected to yield strong screening above the bulk superconducting temperature[35,36,40]. Therefore, one could phenomenologically describe the role of SF in underdoped compounds, as follows. At $T \gg T_c$, just below T^*, fluctuating pairs are formed, without long-range phase coherence. Below T_{SF}, about $20-30$ K above T_c, phase coherence among adjacent charge-rich drops[36] start to develop, yielding the formation of superconducting loops with strong screening and causing the onset of the anomalous diamagnetism. Close to T_c, SF of GL character occur and long-range phase coherence sets in.

V. SUMMARIZING REMARKS AND CONCLUSIONS

By combining magnetization and NMR-NQR relaxation measurements, an attempt has been done to clarify the role of superconducting fluctuations and of fluctuating diamagnetism in underdoped YBCO, vis-a-vis the optimally doped compound. In the latter case the fluctuations above T_c are rather well described by an anisotropic Ginzburg-Landau (GL) functional and by scaling arguments for slightly anisotropic systems. A breakdown of the Gaussian approximation for small magnetic fields has been observed close to T_c. The ^{63}Cu relaxation rates W around T_c show little field dependence, if any. One cannot rule out the presence of a MT contribution, and then of a small $s-$wave component in the spectrum of the fluctuations, which should be sample-dependent in view of the role of impurities in the pair-breaking mechanisms. In underdoped YBCO an anomalous diamagnetism is observed, on a large temperature range. The diamagnetic susceptibility at T_c is about an order of magnitude larger than the one in the optimally doped sample and the isothermal magnetization curves cannot be described by the anisotropic GL functional. Scaling arguments, such as the search of an universal function in terms of $\epsilon/H^{1/2\nu}$, appear inadequate to justify the experimental findings. The anomalies are more marked in the chain-ordered samples. Also in the underdoped YBCO ^{63}Cu W in NQR almost coincide with the NMR ones at $H = 9.4$ Tesla, in agreement with a theoretical estimate of the effect of the magnetic field. Another conclusion drawn from the field and temperature dependences of the ^{63}Cu relaxation rate is that the spin gap does not depend on the magnetic field and that the behavior of the spin susceptibility for $T \gg T_c$ cannot be ascribed to SF of GL character.

The fluctuating diamagnetism observed in underdoped YBCO can be phenomenologically accounted for by the presence of charge inhomogeneities at mesoscopic level. The anomalies in the magnetization curves can be attributed to "locally superconducting" non-percolating drops, present above the bulk T_c and favoured by chain ordering.

VI. ACKNOWLEDGEMENTS

A. Bianconi, F. Borsa, J. R. Cooper and M. H. Julien are thanked for useful discussions. The collaboration of Paola Mosconi in processing the SQUID magnetization data is gratefully acknowledged. Thanks are due to B.J. Suh and P. Manca, for having provided well characterized underdoped YBCO compounds. The availability of the Metronique Ingegnerie SQUID magnetometer from the Departement of Chemistry, University of Florence (Prof. D. Gatteschi) is gratefully acknowledged. The research has been carried out in the framework of a "Progetto di ricerca avanzata (PRA)", sponsored by Istituto Nazionale di Fisica della Materia (PRA-SPIS 1998-2000).

REFERENCES

[1] For a recent collection of papers, see " Fluctuations Phenomena in High Temperature Superconductors", Edited by M. Ausloos and A.A. Varlamov, Kluwer Academic Publisher, (1997)

[2] A.A. Varlamov, G.Balestrino, E. Milani and D.V. Livanov, Advances in Physics 48, 655 (1999)

[3] M.Thinkham "Introduction to Superconductivity", Mc Graw-Hill N.Y. (1996) Chapters 8-9

[4] See A.Junod, in "Studies of High Temperature Superconductors", edited by A.V. Narlikar (Nova Science Publishers, Inc. New York, 1996), Vol. 18

[5] V.Pasler et al. Phys. Rev. Lett. 81, 1094 (1998)

[6] Z.H. Lin et al. Europhys. Letters 32, 573 (1995) and references therein

[7] M.A. Howson et al. Phys. Rev. B 51, 11984 (1995) and references therein

[8] See the review paper by L.N.Bulaevskii, Int. J. of Modern Physics B4, 1849 (1990) and several papers in Ref. 1

[9] P.Carretta, D. Livanov, A.Rigamonti and A.A.Varlamov, Phys.Rev.B 54, R9682 (1996)

[10] P.Carretta, A.Rigamonti, A.A.Varlamov, D.Livanov, Nuovo Cimento 19 , 1131 (1997)

[11] V. Mitrovic et al., Phys. Rev. Lett. 82, 2784 (1999)

[12] H.N.Bachman et al., Phys. Rev. B 60, 7591 (1999)

[13] K. Gorny et al., Phys. Rev. Lett. 82, 177 (1999)

[14] M. Eschrig et al., Phys. Rev. B 59, 12095 (1999)

[15] M.Randeira and A.A.Varlamov, Phys. Rev. B 50, 10401 (1994)

[16] A.Rigamonti, F.Borsa and P.Carretta, Rep.Prog.Phys.61, 1367 (1998)

[17] A.G. Loeser et al. Science 273, 325 (1996)

[18] H.Ding et al. Nature 382, 51 (1996)

[19] G. V. M. Williams, J. L. Tallon, R. Michalak and R. Dupree, Phys. Rev. B 54, R6909 (1996)

[20] T. Dahm, D. Manske and L. Tewordt, Phys. Rev. B 55, 15274 (1997)

[21] V.J.Emery, S.A.Kivelson and O.Zachar Phys.Rev. B 56, 6120 (1997); see also V. J. Emery and S. A. Kivelson, J. Phys. Chem. Sol. 59, 1705 (1998)

[22] C. Castellani, C. Di Castro and M. Grilli Z.Phys. B 103, 137 (1997)

[23] C.Baraduc, A. Budzin, J-Y Henry, J.P. Brison and L. Puech, Physica C 248 138 (1995)

[24] A.Budzin and V.Dorin, Ref. 1, p.335

[25] M. B. Salamon et al. Phys.Rev. B 47, 5520 (1993)

[26] T.Schneider and H. Keller, Inter. Jornal of Modern Physics B 8, 487 (1993)

[27] A.Junod, J.Y. Genoud, G. Triscone and T. Schneider, Physica C 294, 115 (1998)

[28] R.E. Prange, Phys. Rev. B 1, 2349 (1970)

[29] M.A.Hubbard, M.B. Salamon and B.W.Veal, Physica C 259, 309 (1996)

[30] C.P.Slichter "Principles of Magnetic Resonance", Springer Verlag, Berlin-Heidelberg (1990)

[31] P.Manca, P.Sirigu, G.Castellani and A.Migliori, Il Nuovo Cimento 19, 1009 (1997); G.Castellani, A.Migliori, P.Manca and P.Sirigu, Il Nuovo Cimento 19, 1075 (1997)

[32] U.Welp et al., Phys.Rev.Lett. 67, 3180 (1991)

[33] A.I.Buzdin and A.A.Varlamov, Phys.Rev.B 58, 14195 (1998)

[34] P.Mosconi, A.Rigamonti and A. A. Varlamov, Appl. Mag. Reson. to be published

[35] Yu. N. Ovchinikov, S. A. Wolf and V. Z. Kresin, Phys. Rev. B 60, 4329 (1999)

[36] E. Z. Kuchinskii and M. V. Sadovskii, cond-mat/9910261

[37] D.Mihailovic, T.Mertelj and K.A.Muller, Phys. Rev. B 57, 6116 (1998); see also Kabanov et al. Phys.Rev.B 59, 1497 (1999)

[38] M. R. Norman, cond-mat/9904048

[39] A.Bianconi et al. Phys.Rev.Lett. 76, 3412 (1996)

[40] C. Bergemann et al., Phys. Rev. B 57, 14387 (1998)

FIGURES

FIG. 1. *a)* NMR spectrum of the ^{63}Cu(2) satellite line and the correspondent relaxation law (*b*) (the solid line is the best fit according to Eq. 8 in the text).

FIG. 2. *a)* NQR (o) and NMR (□) ($H_o = 6$ Tesla $\parallel \vec{c}$) ^{63}Cu relaxation rates $2W$ in optimally doped YBCO. The solid and dashed lines are guides for the eye. The dotted line is the temperature behavior according to Eq. 7 in the text for $r = 0$ (namely 2D spectrum of fluctuations) and $\gamma_\phi = 0.2$. NQR (empty simbols) and NMR (full symbols) relaxation rates $2W$ (in a field of 9.4 Tesla along the c-axis) in chain-disordered (*b*) and chain-ordered (*c*) underdoped YBCO around T_c.

FIG. 3. Raw data for M/H ($H = 0.1$ Tesla) in chain-ordered YBCO, for field along the c-axis (□) and in the a-b plane (△). In the inset the results for H_{c2} around T_c are shown (estimated experimental error ≤ 2 %). The solid lines indicate the procedure to evaluate $T_c(H)$ and $T_c(0)$.

FIG. 4. Ratio M/H, in a field of 0.02 Tesla along the c-axis, in chain-ordered YBCO. The inset is the blow-up of the data for $T \geq 85K$. Similar results have been obtained in another sample prepared with the same procedure.

FIG. 5. Comparison of the susceptibility (defined as M/H, for $H = 0.02$ Tesla along the c-axis) in optimally doped YBCO (squares) and in chain-disordered (circles) and chain-ordered (triangles) underdoped YBCO.

FIG. 6. Evidence of the failure of anisotropic GL functional and of scaling arguments to describe the magnetization curves in underdoped YBCO. The solid lines in the upper part of the figure are the behaviours obtained from the numerical derivative of Eq. 2. The dashed lines are guides for the eye.

FIG. 7. Magnetization curve in chain-ordered underdoped YBCO under high stabilization temperature ($T = 65.67K$). *a)* raw data for the total magnetization, *b)* fluctuating magnetization M_{fl} as a function of the field.

	YBCO	YBCO		
	optimally doped	underdoped		
		disordered	chain-ordered	
$T_c(0)$	$91.1 \pm 0.4\ K$	$63.3 \pm 0.4\ K$	$64.5 \pm 0.4\ K$	$64.2 \pm 0.4\ K$
$T_c(H = 6Tesla)$	$87 \pm 0.5\ K$	$60 \pm 1\ K$	-	-
$T_c(H = 9.4Tesla)$	-	$55 \pm 1\ K$	$54 \pm 1\ K$	-
$\left(\frac{\partial H_{c2}}{\partial T}\right)_{T_{c0}}\ T/K$	-1.2 ± 0.2	-1.05	-1.1 ± 0.2	-1.0 ± 0.1
$H_{c2}(T \to 0) \quad \mathbf{H} \parallel \mathbf{c}$	$100 \pm 20\ T$	$\sim 70\ T$	$\sim 65\ T$	-
$H_{c2}(T \to 0) \quad \mathbf{H} \perp \mathbf{c}$	$\sim 67\ T$	-	$\sim 44\ T$	-

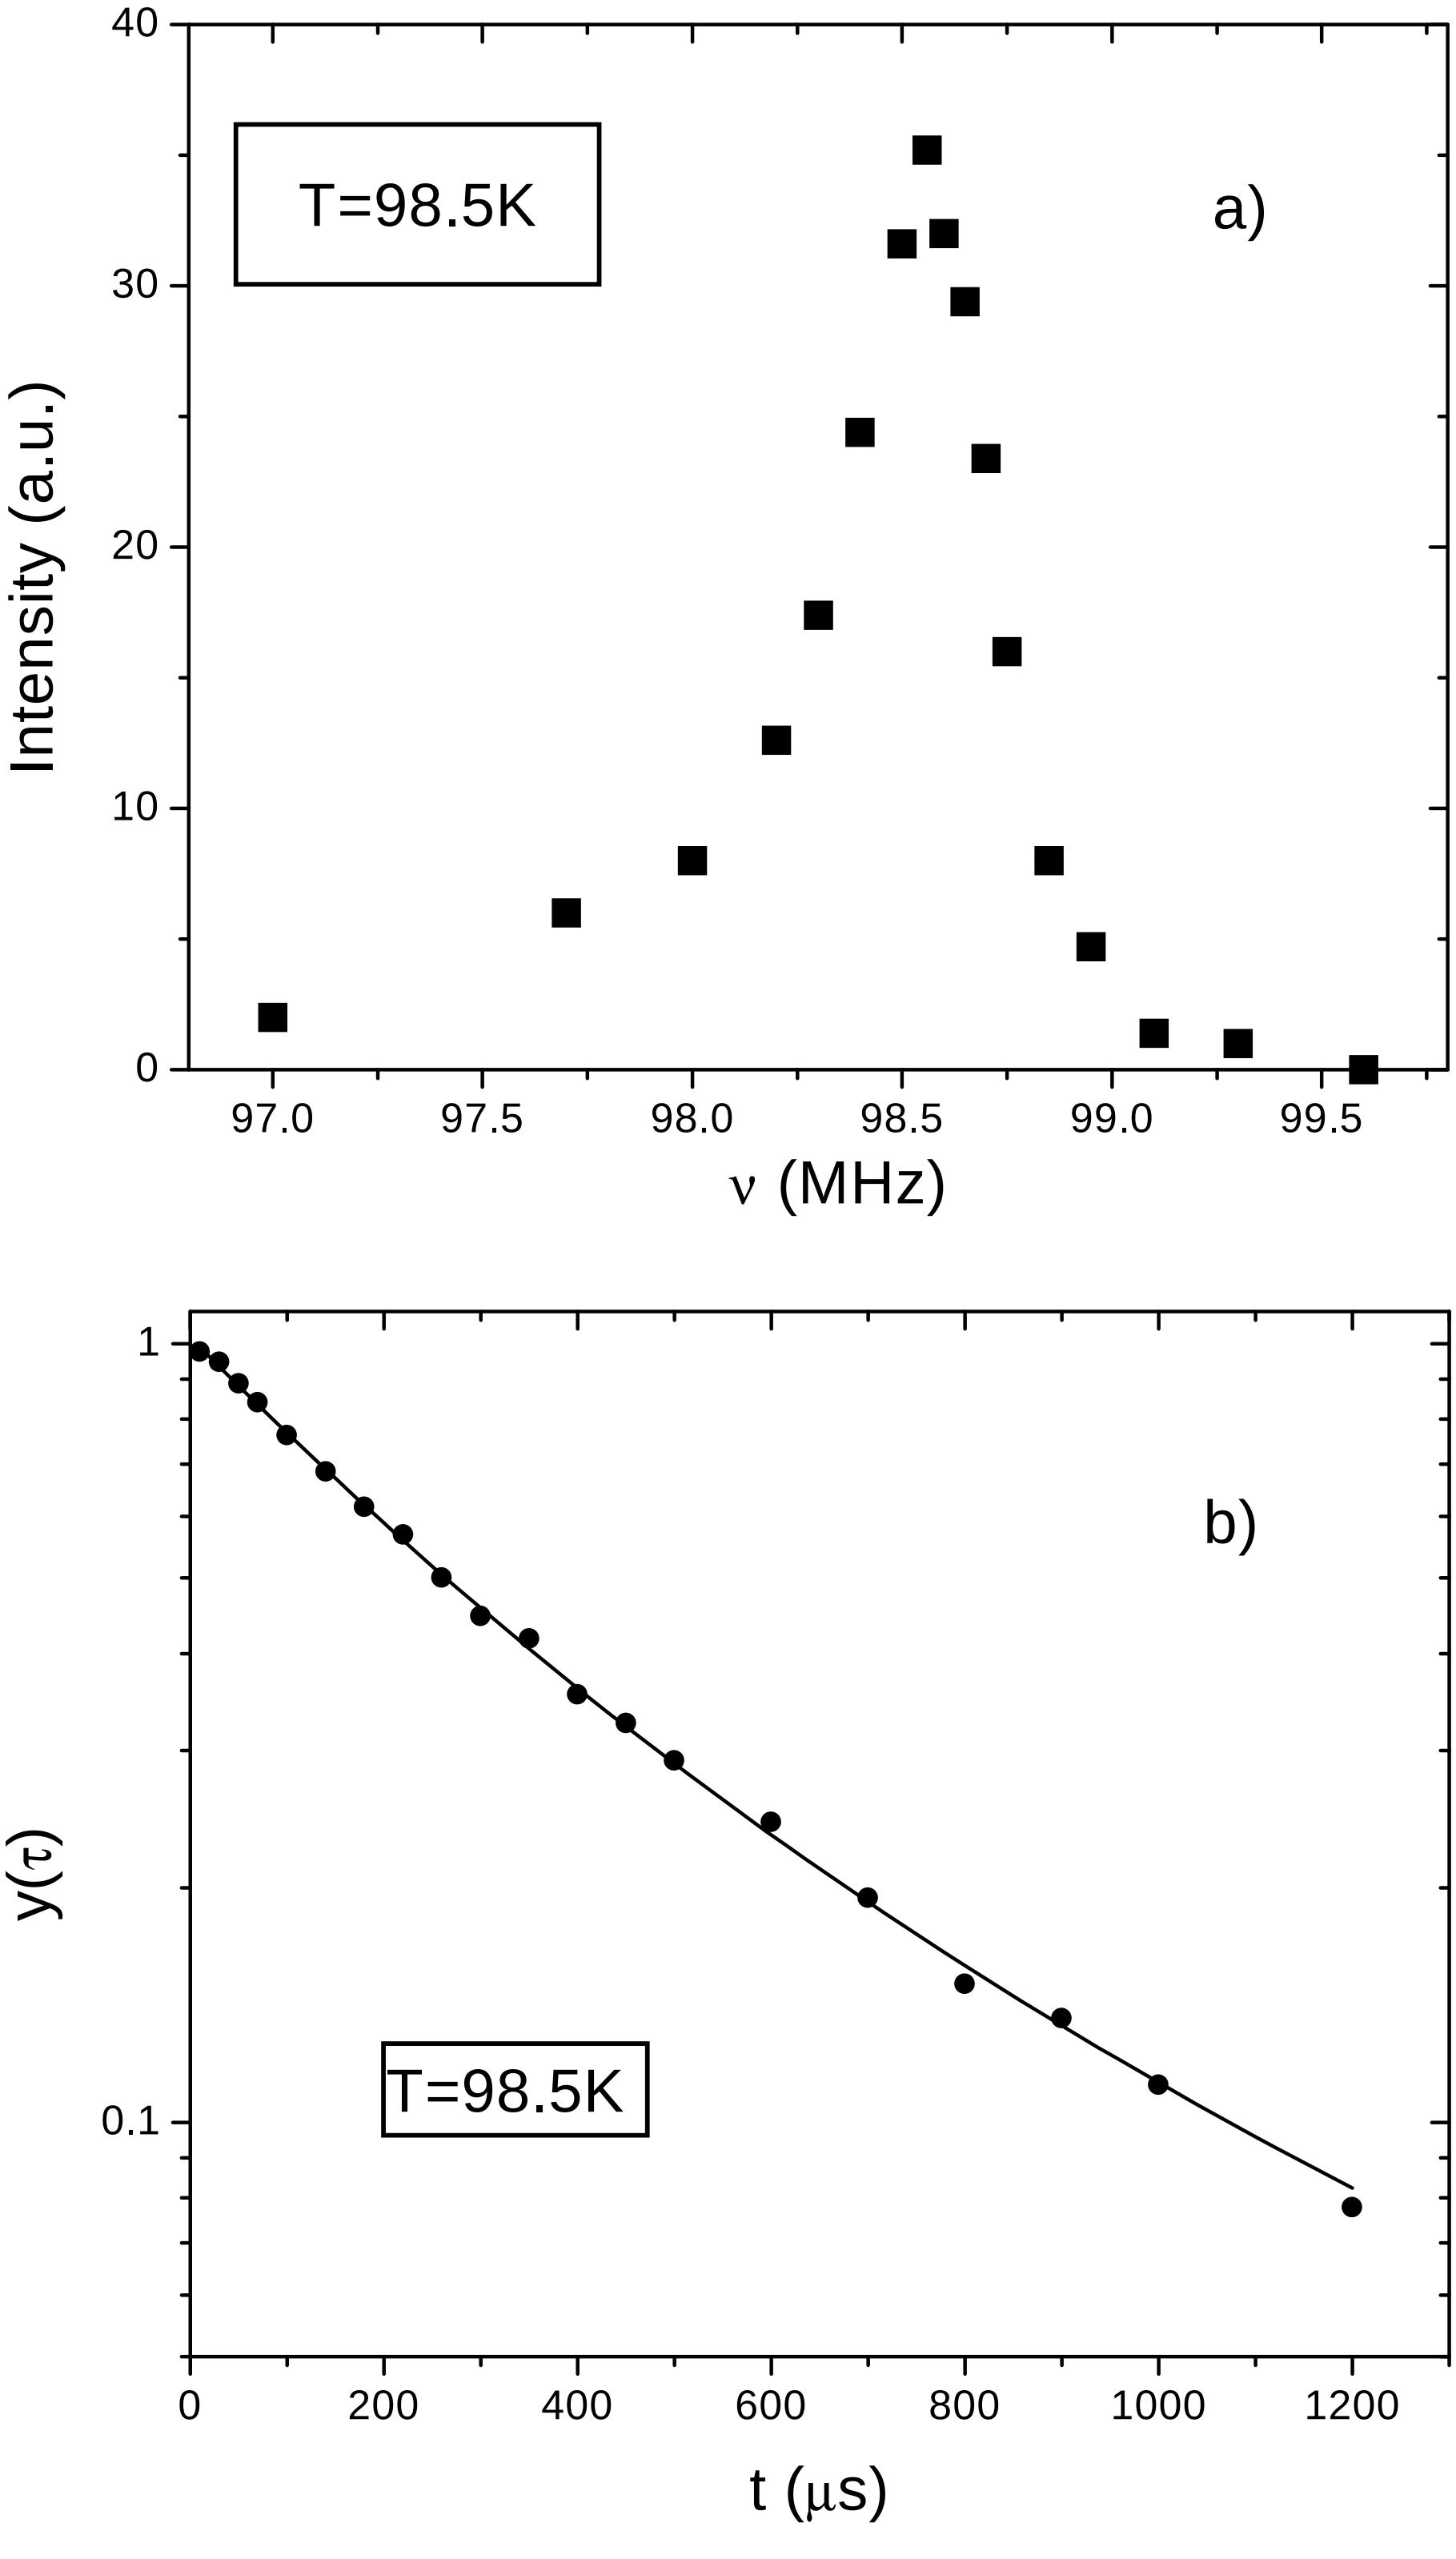

Intensity (a.u.)
0
10
20
30
40
T=98.5K
a)
97.0
97.5
98.0
98.5
99.0
99.5
ν (MHz)
y(τ)
1
0.1
b)
T=98.5K
0
200
400
600
800
1000
1200
t (μs)

Fig. 1

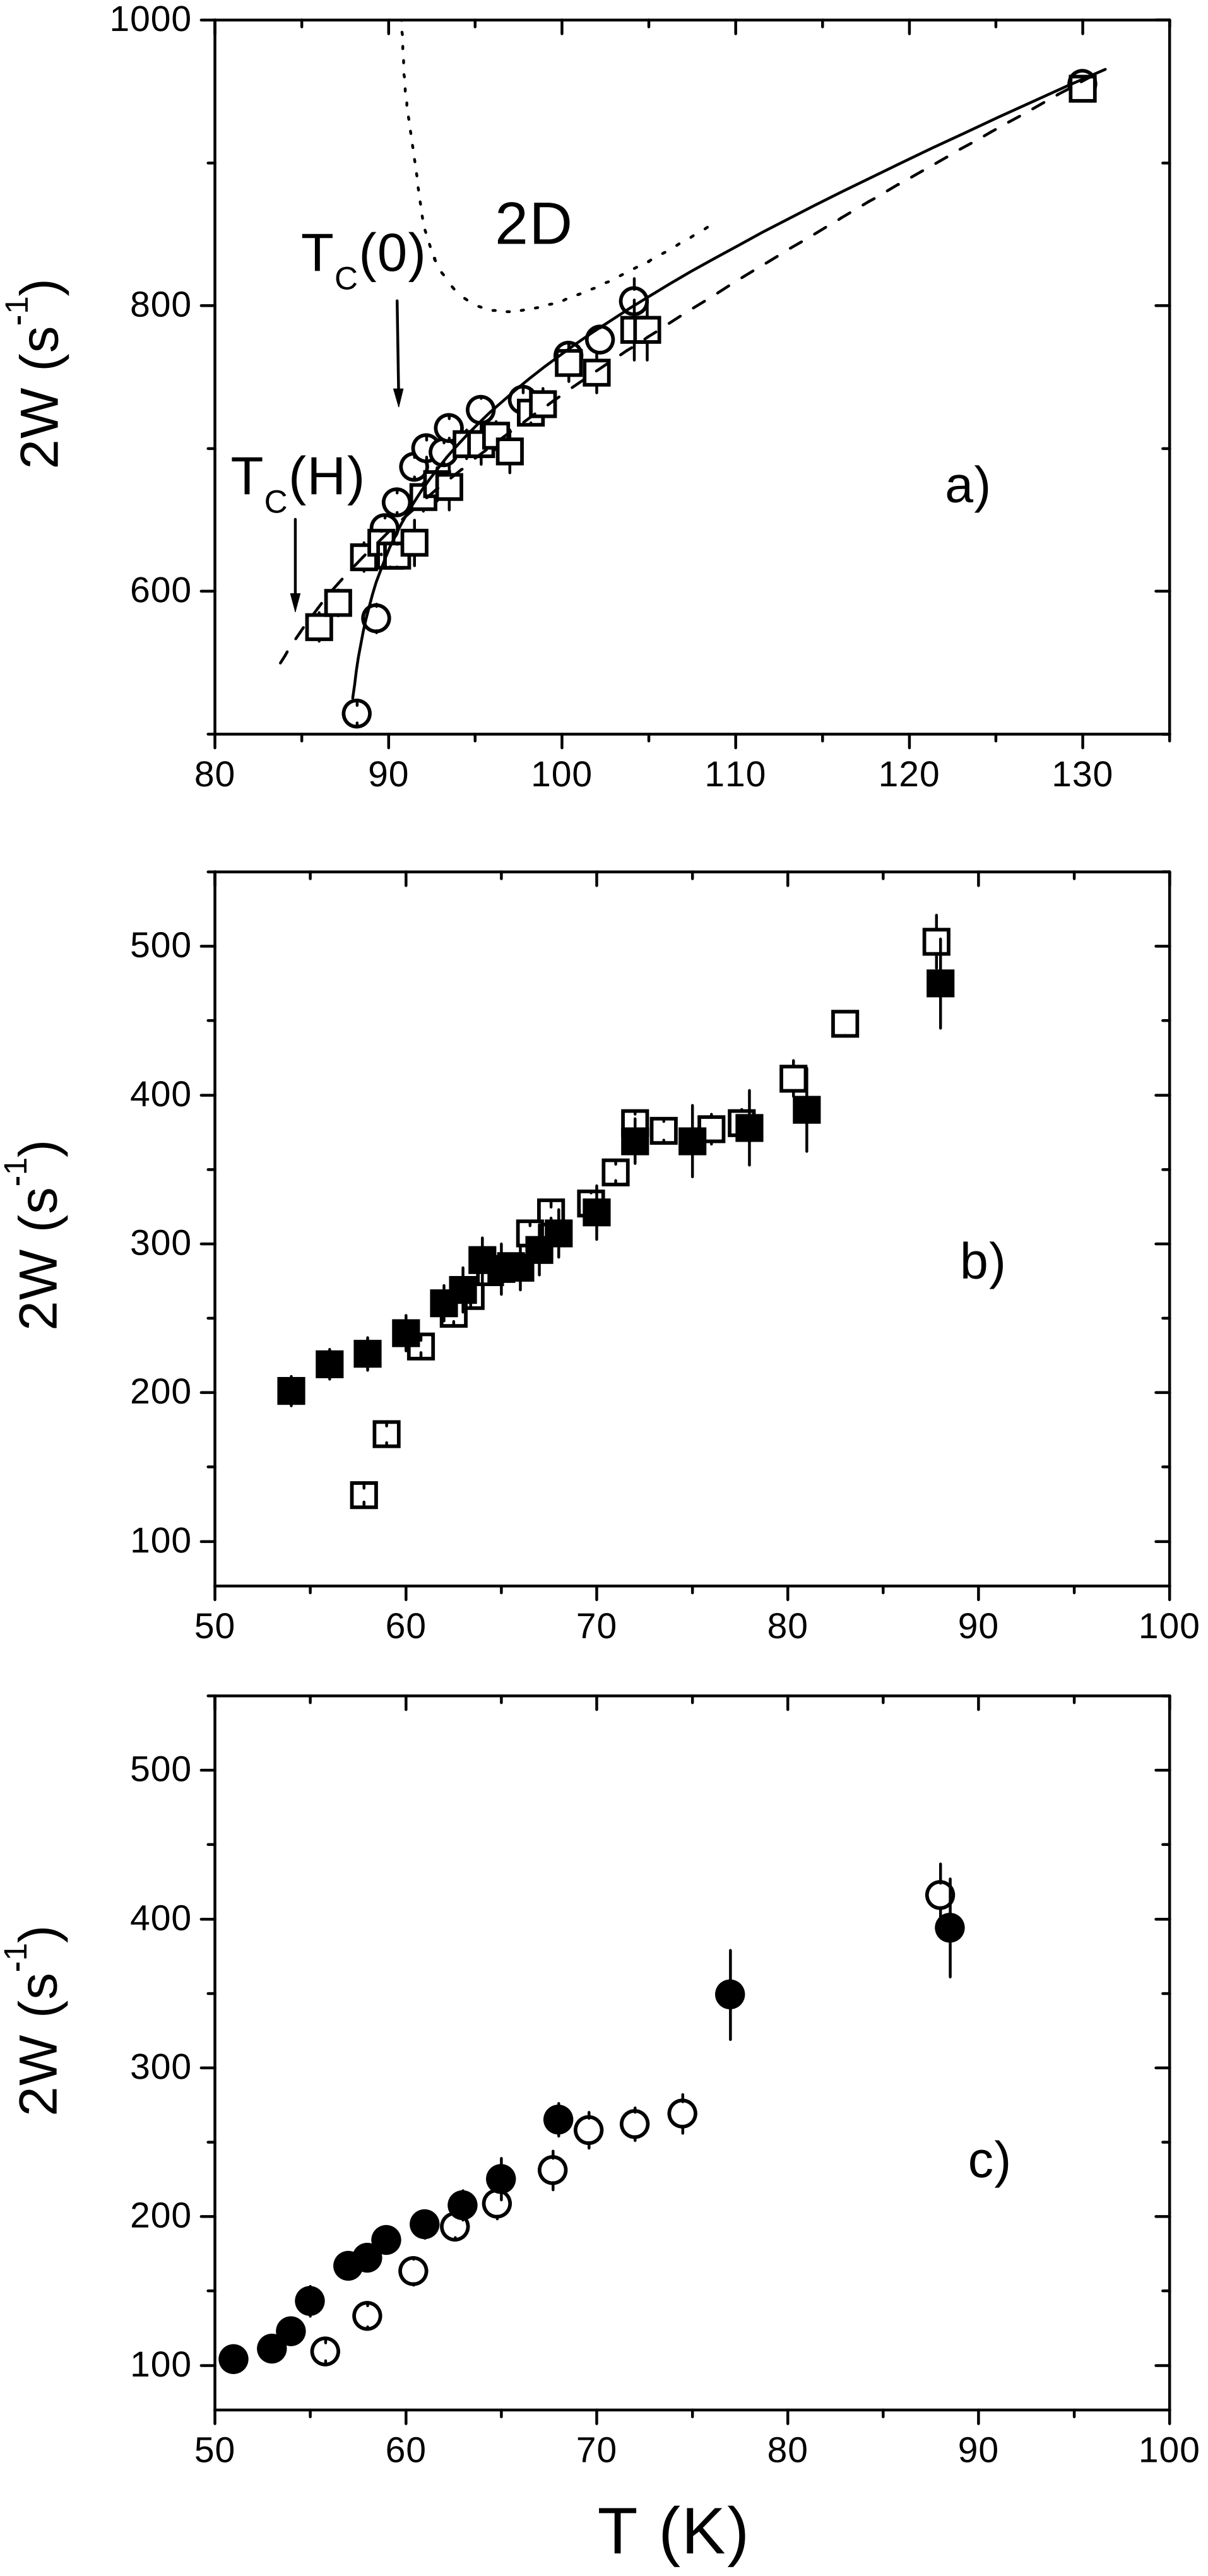
a)
2D
$T_C(0)$
$T_C(H)$
$2W\ (s^{-1})$
1000
800
600
80
90
100
110
120
130
b)
$2W\ (s^{-1})$
500
400
300
200
100
50
60
70
80
90
100
c)
$2W\ (s^{-1})$
500
400
300
200
100
50
60
70
80
90
100
T (K)

Fig. 2

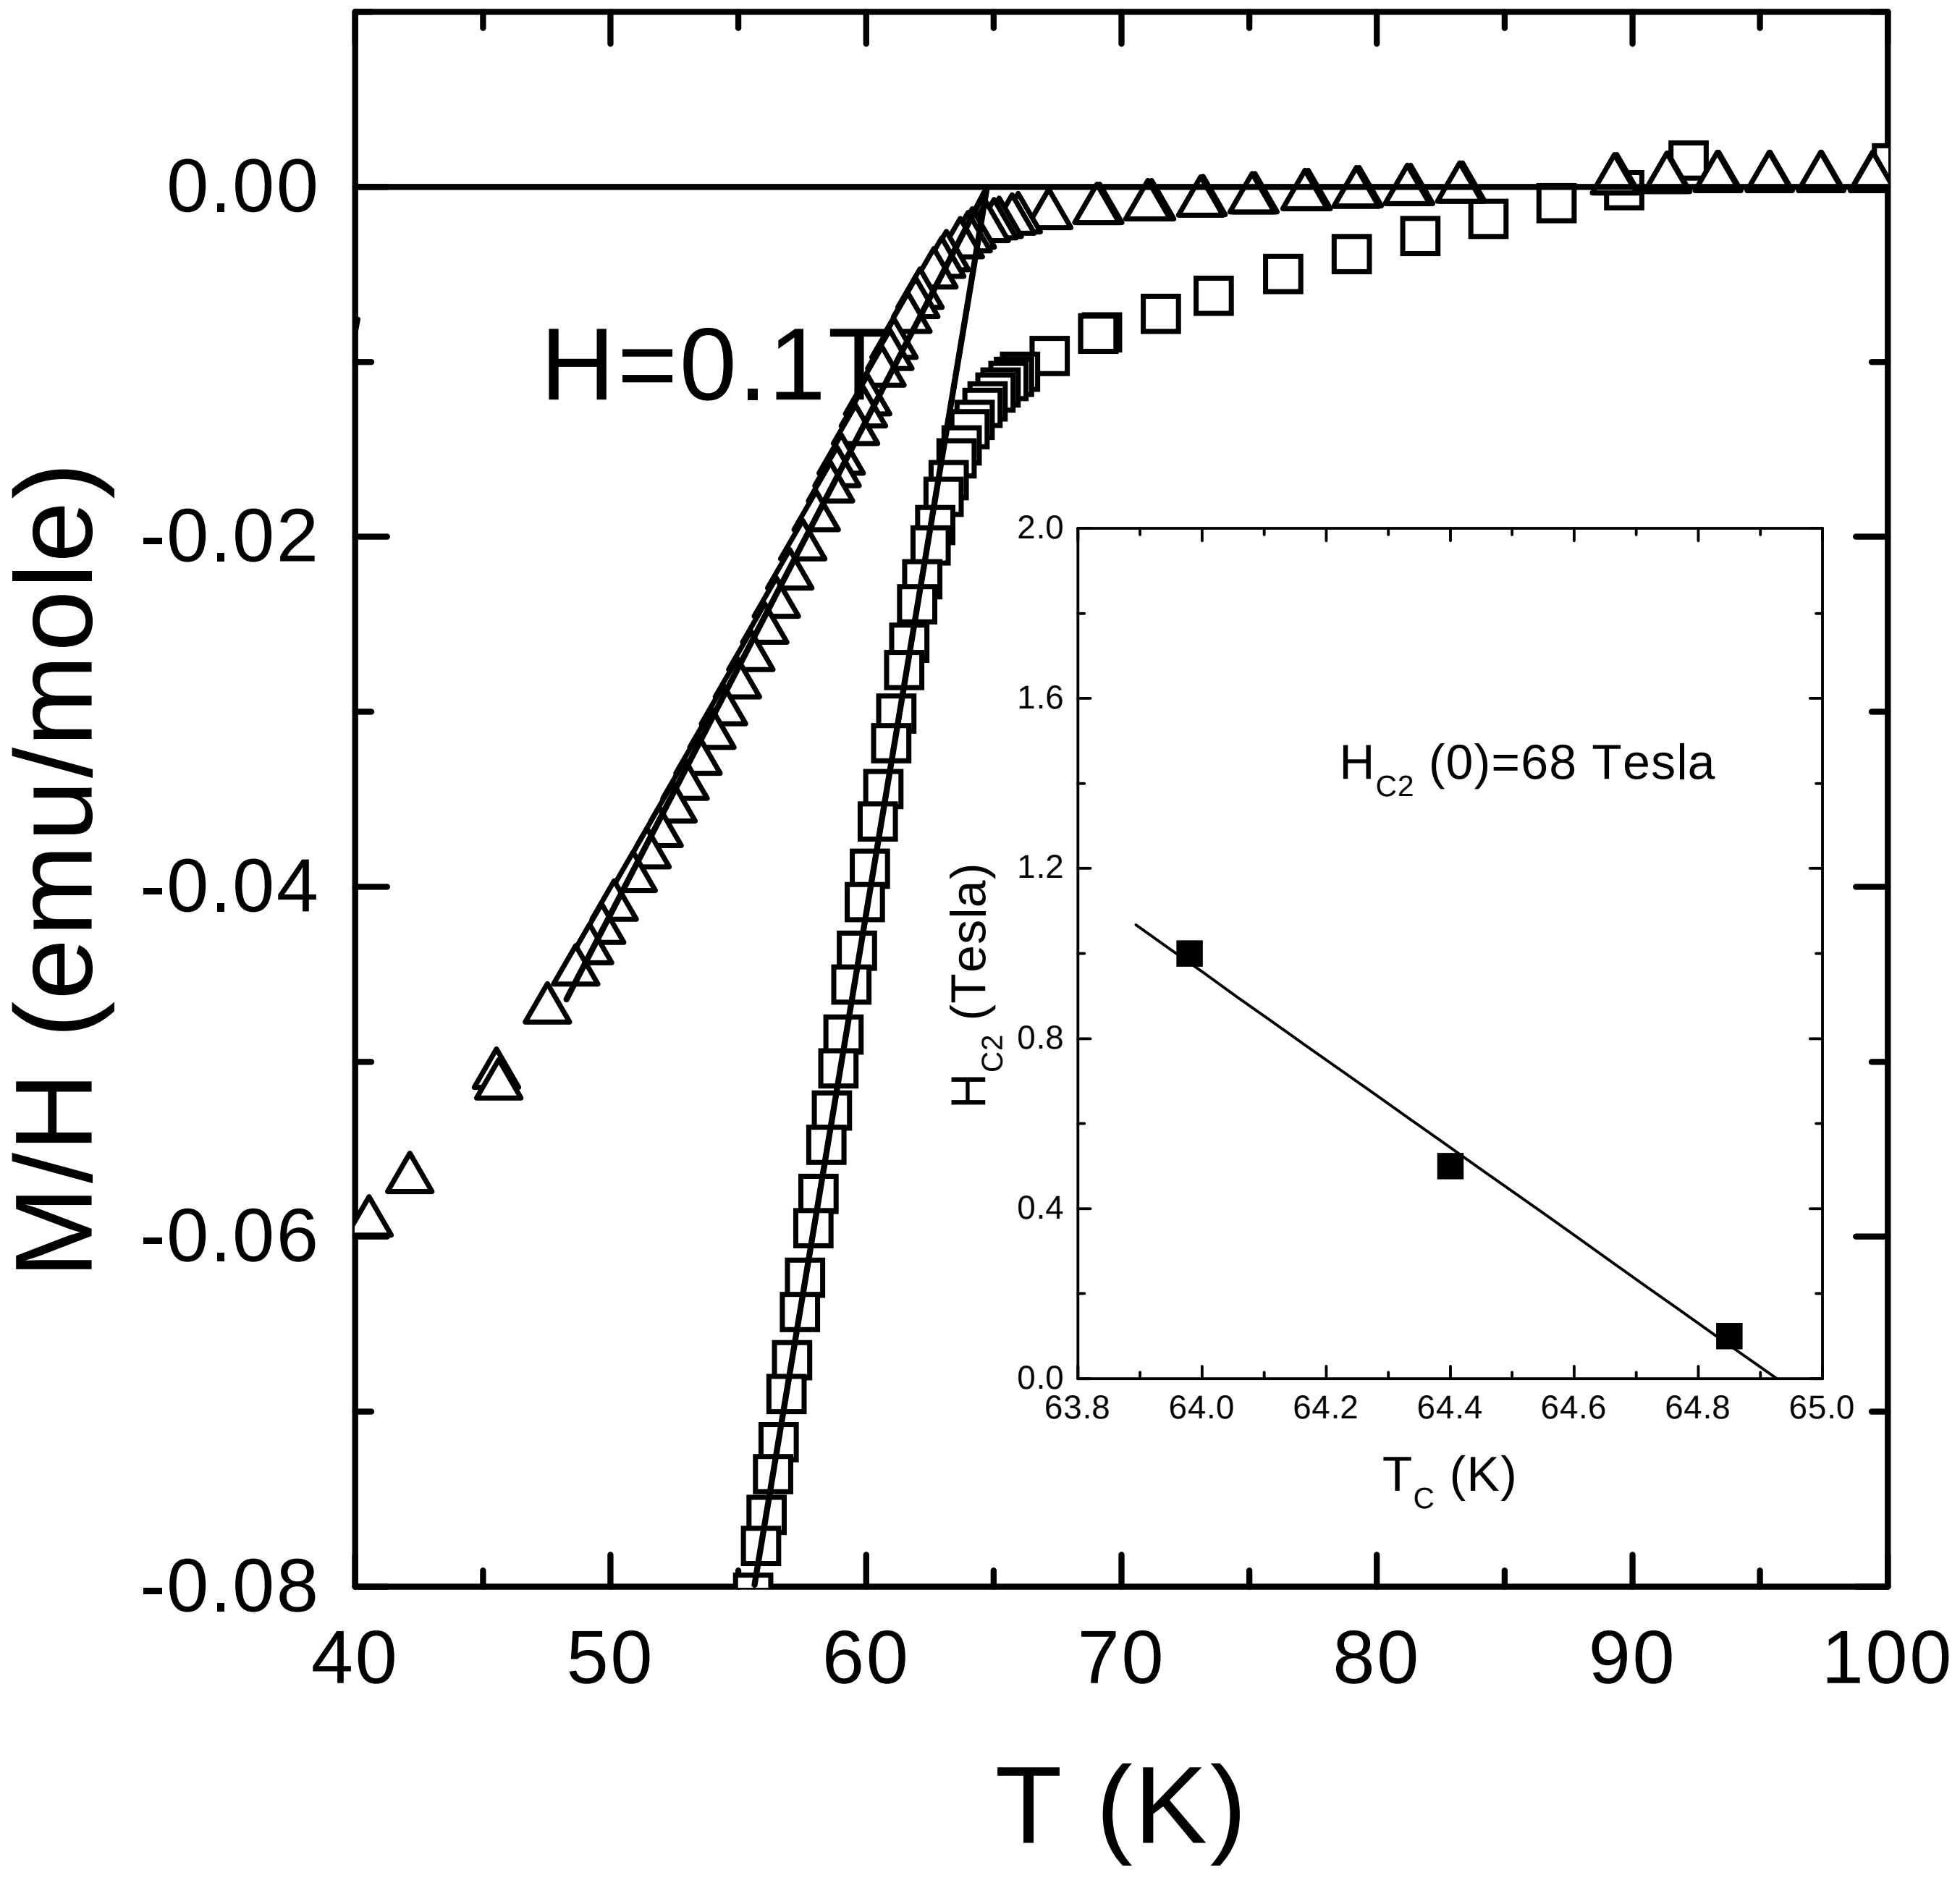
0.00
-0.02
-0.04
-0.06
-0.08
M/H (emu/mole)
40
50
60
70
80
90
100
T (K)
H=0.1T
2.0
1.6
1.2
0.8
0.4
0.0
H_{C2} (Tesla)
63.8
64.0
64.2
64.4
64.6
64.8
65.0
T_C (K)
H_{C2} (0)=68 Tesla

Fig. 3

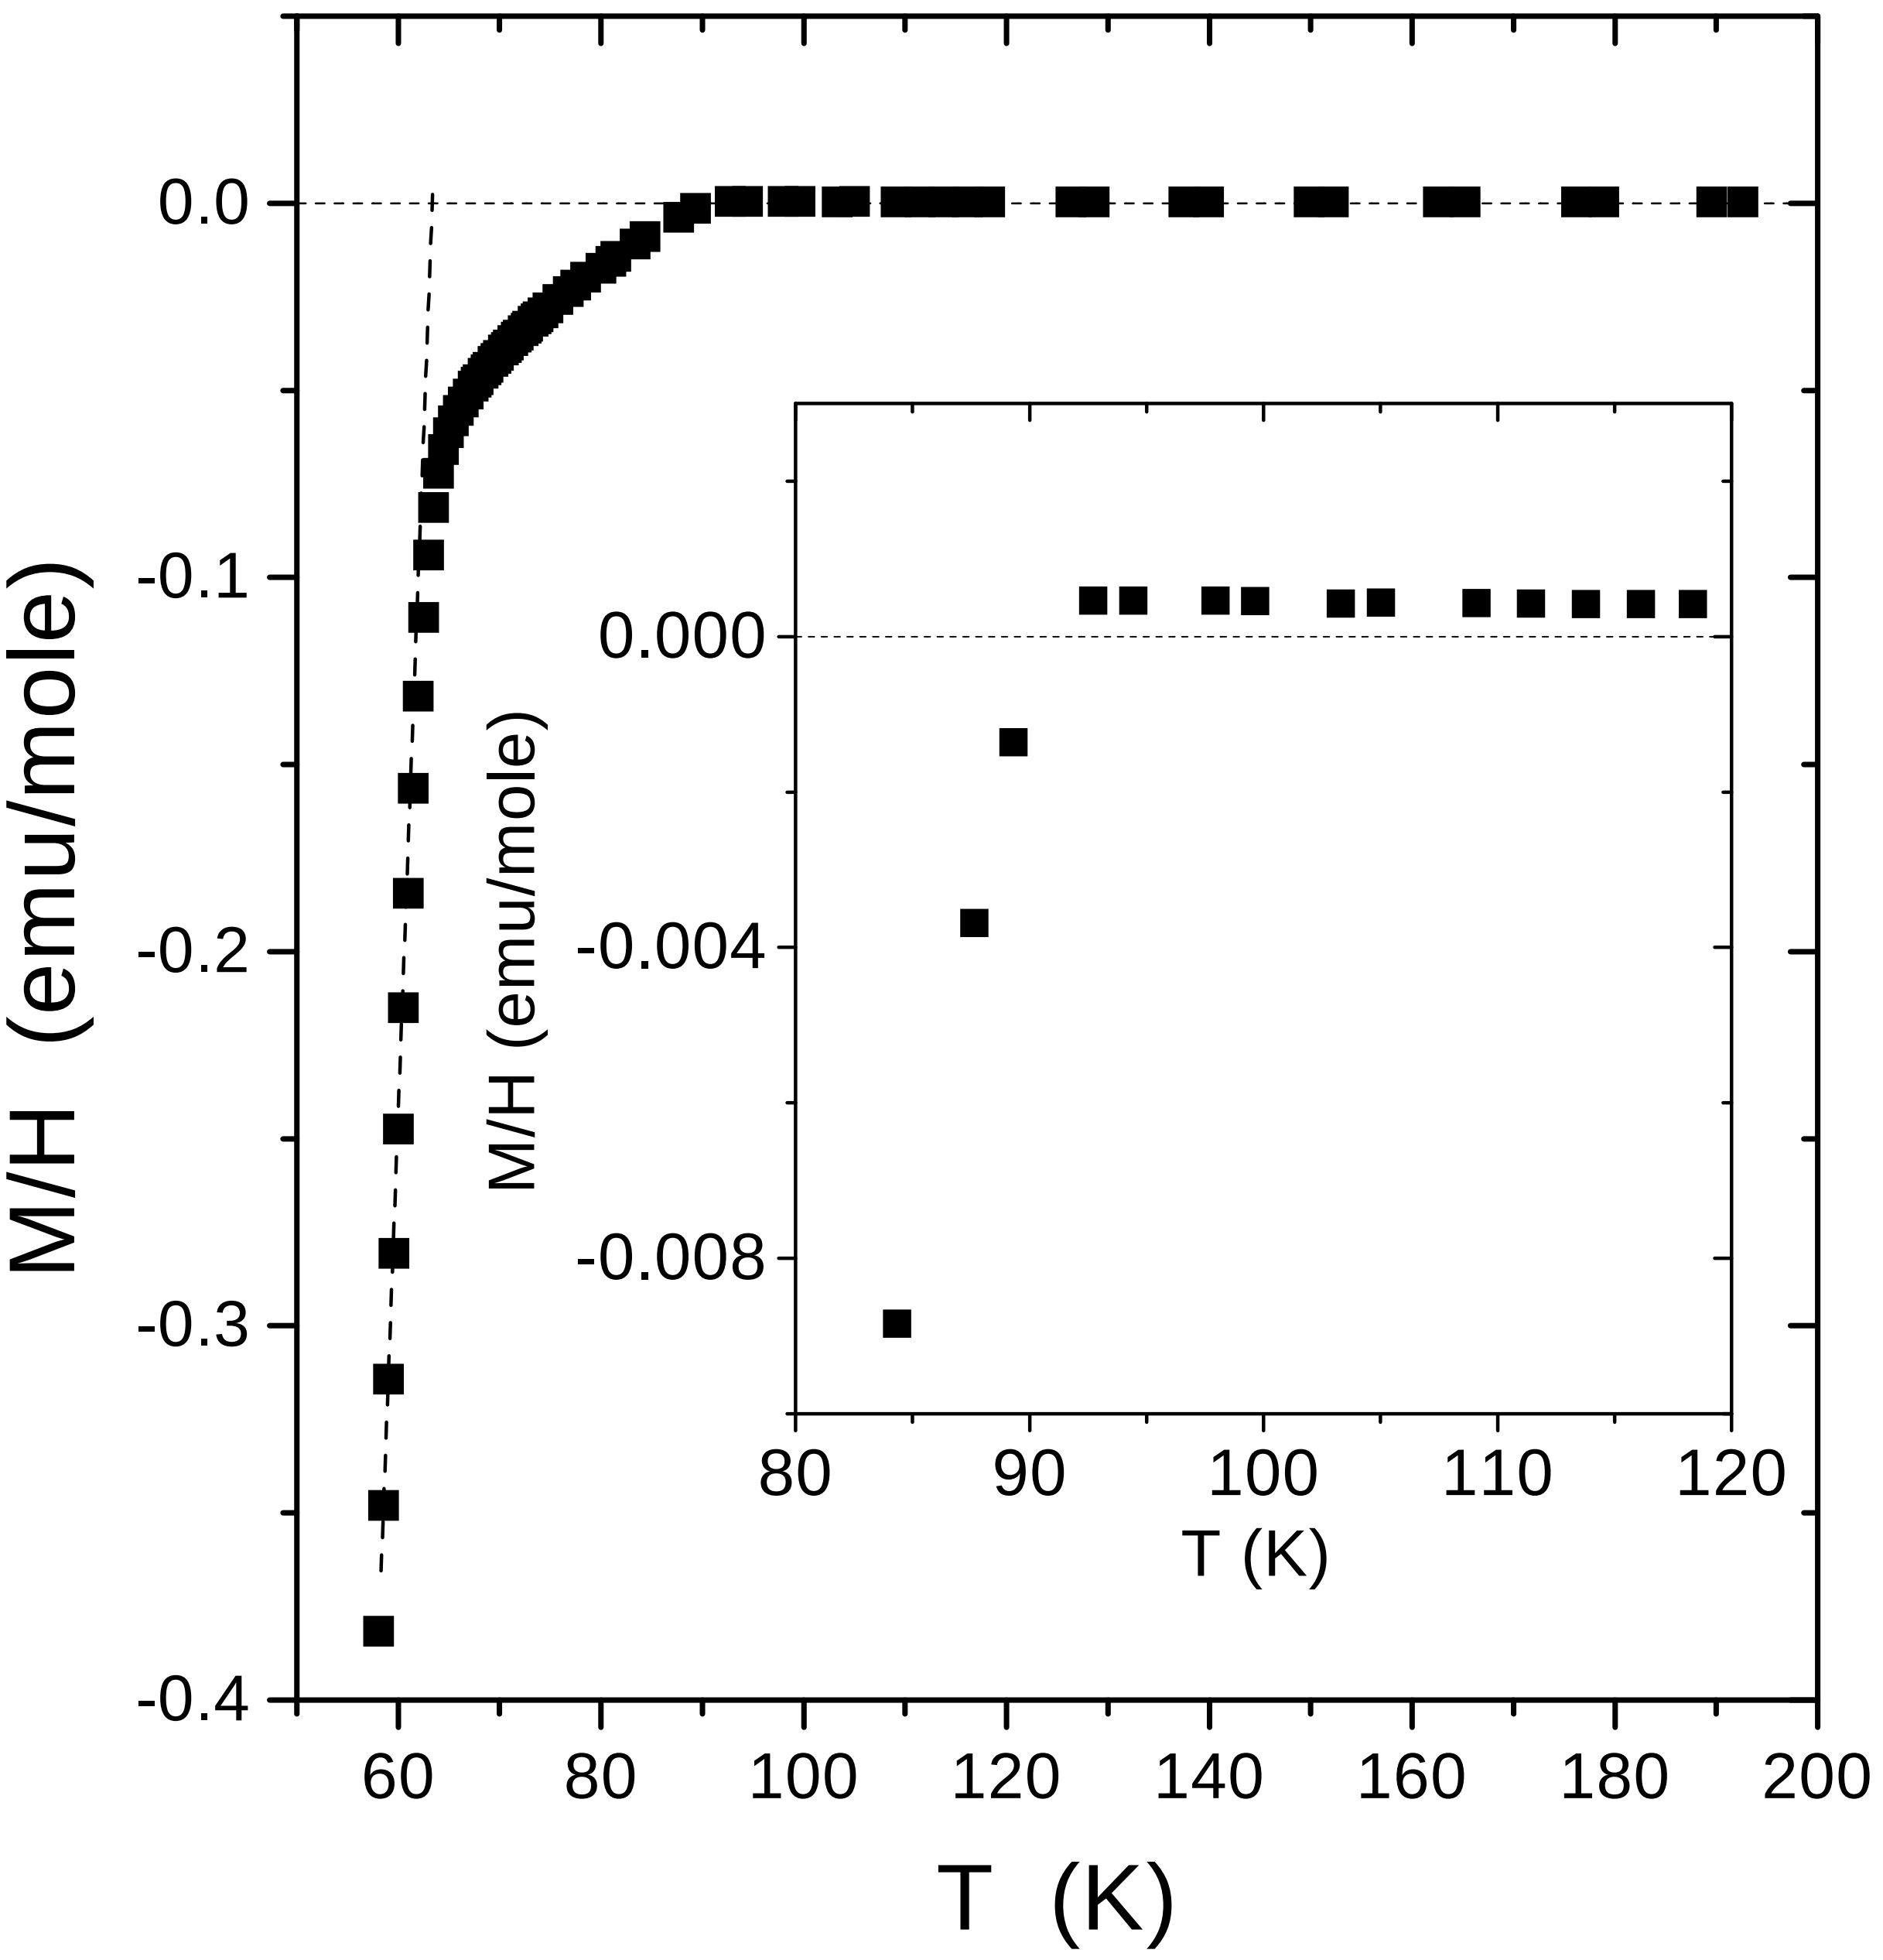
M/H (emu/mole)
0.0
-0.1
-0.2
-0.3
-0.4
60
80
100
120
140
160
180
200
T (K)
M/H (emu/mole)
0.000
-0.004
-0.008
80
90
100
110
120
T (K)

Fig. 4

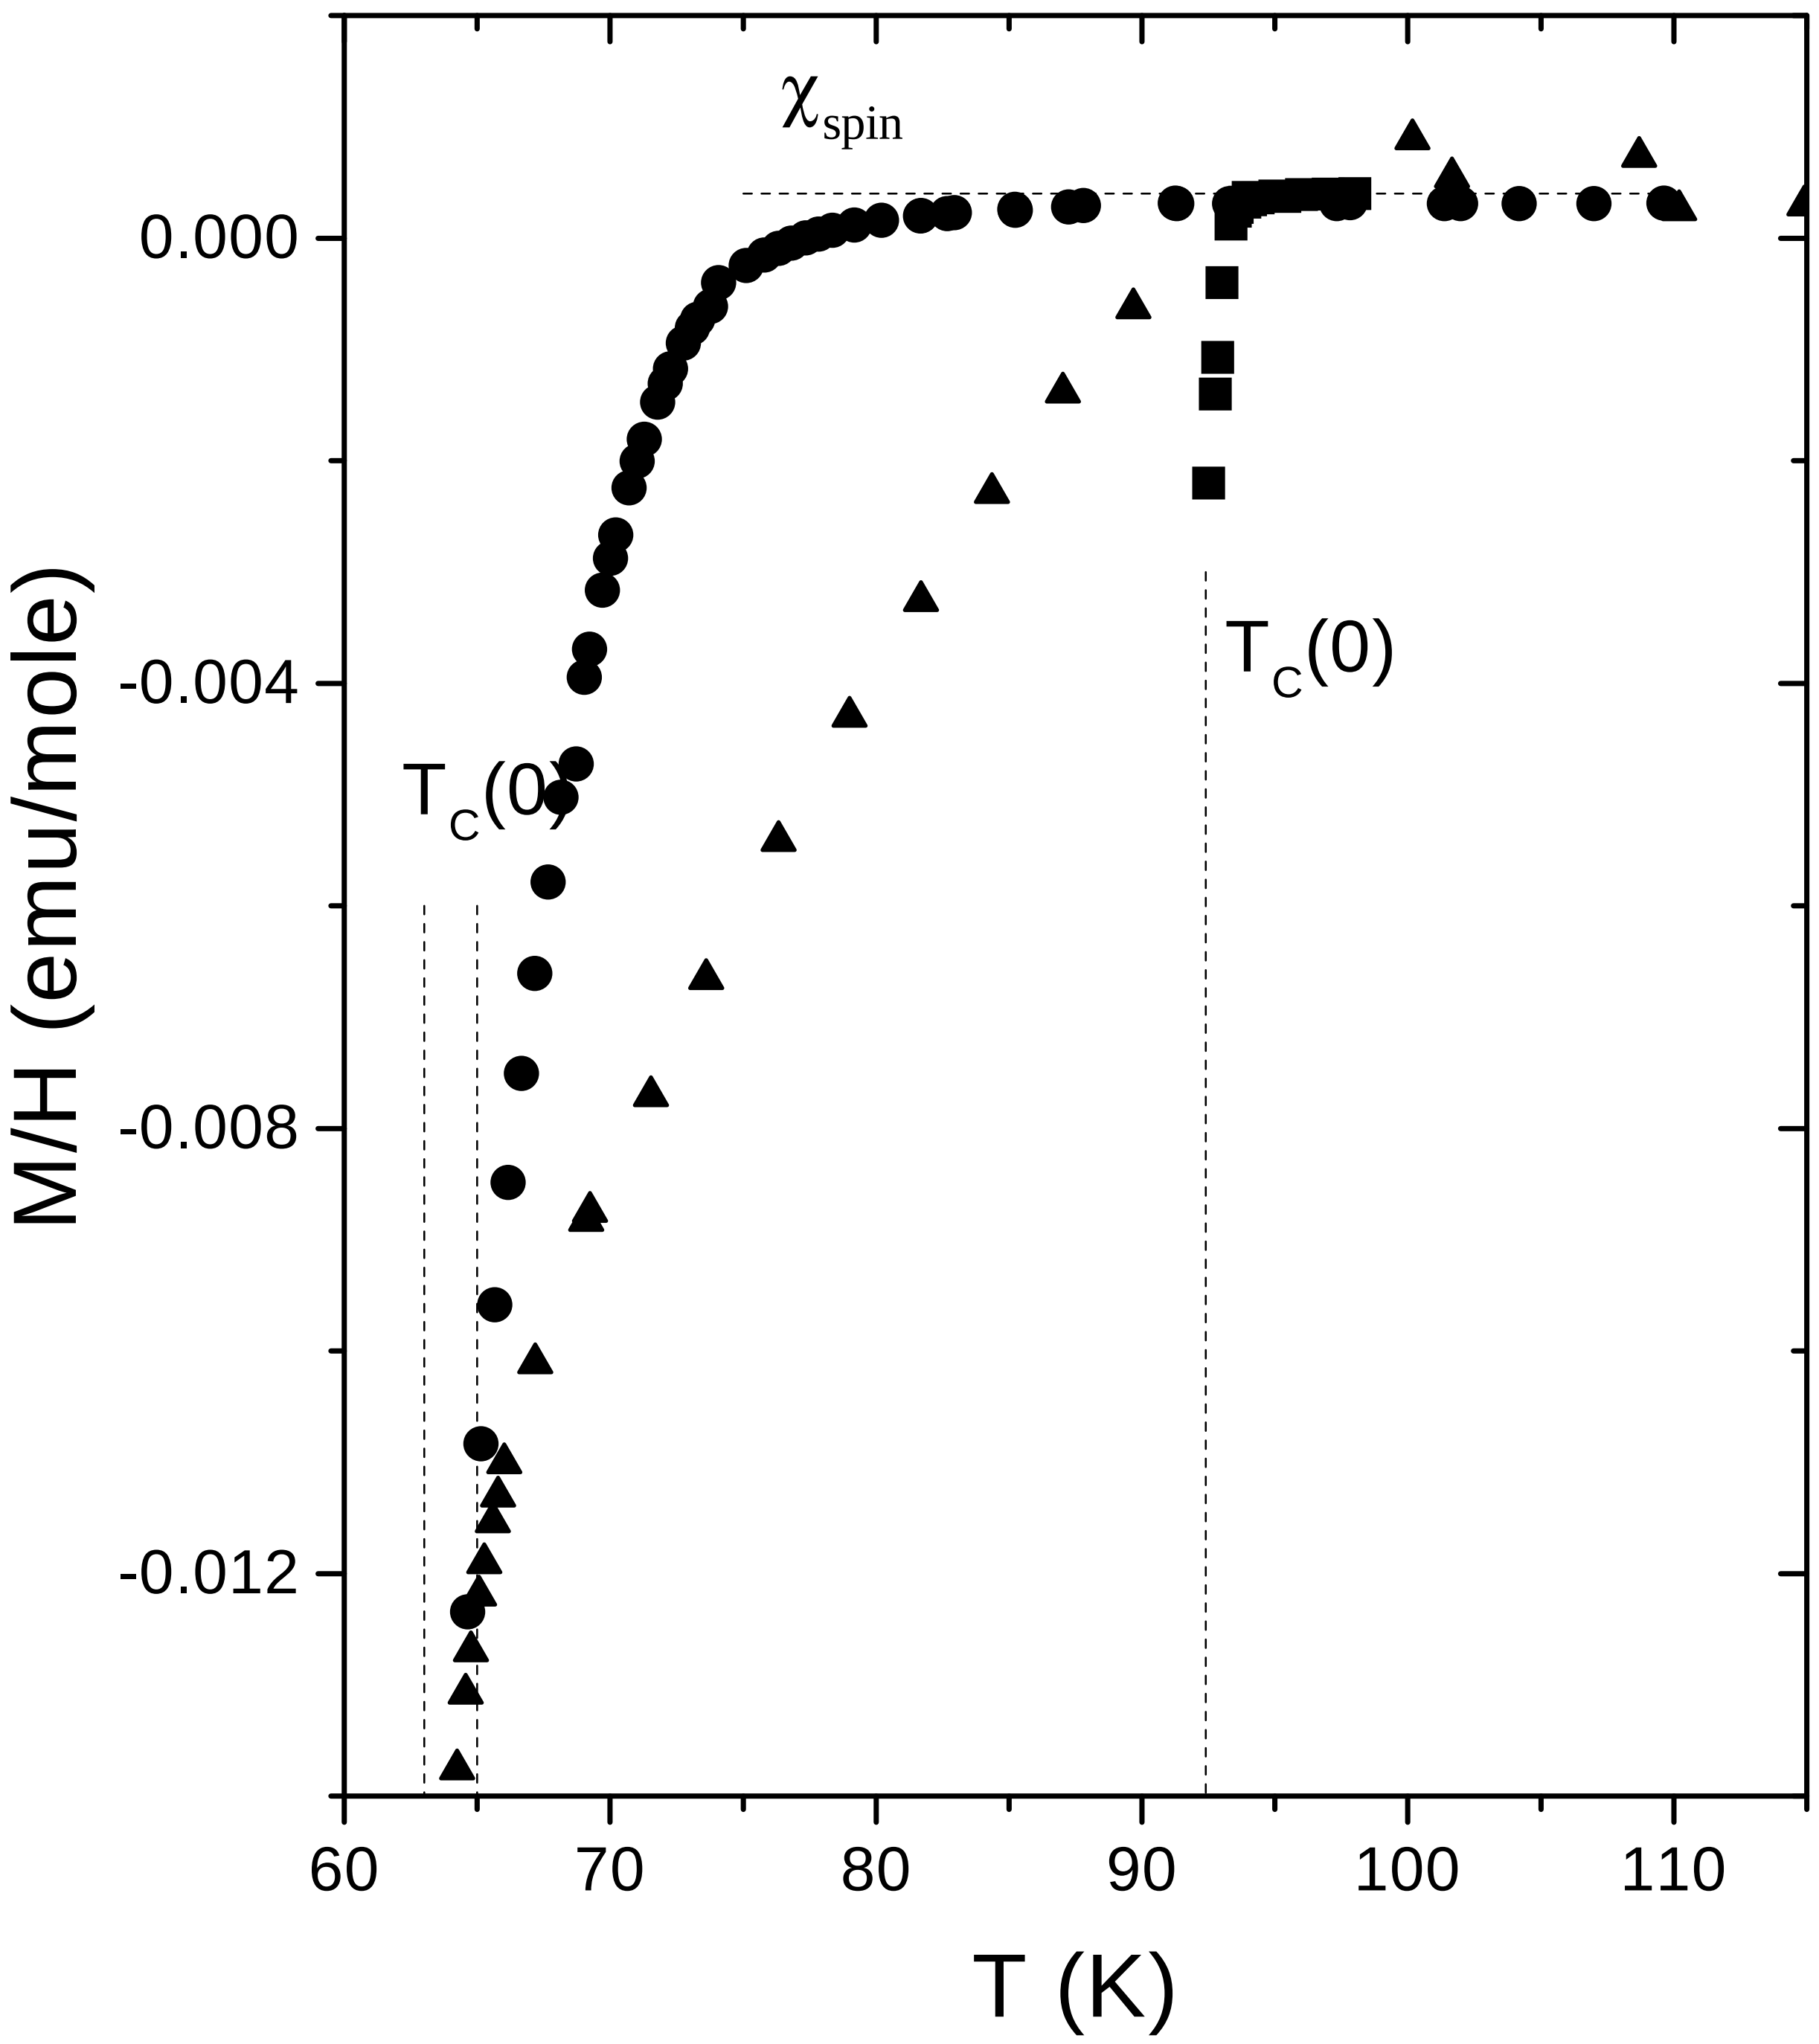
χ_{spin}
0.000
-0.004
-0.008
-0.012
M/H (emu/mole)
$T_C(0)$
$T_C(0)$
60
70
80
90
100
110
T (K)

Fig. 5

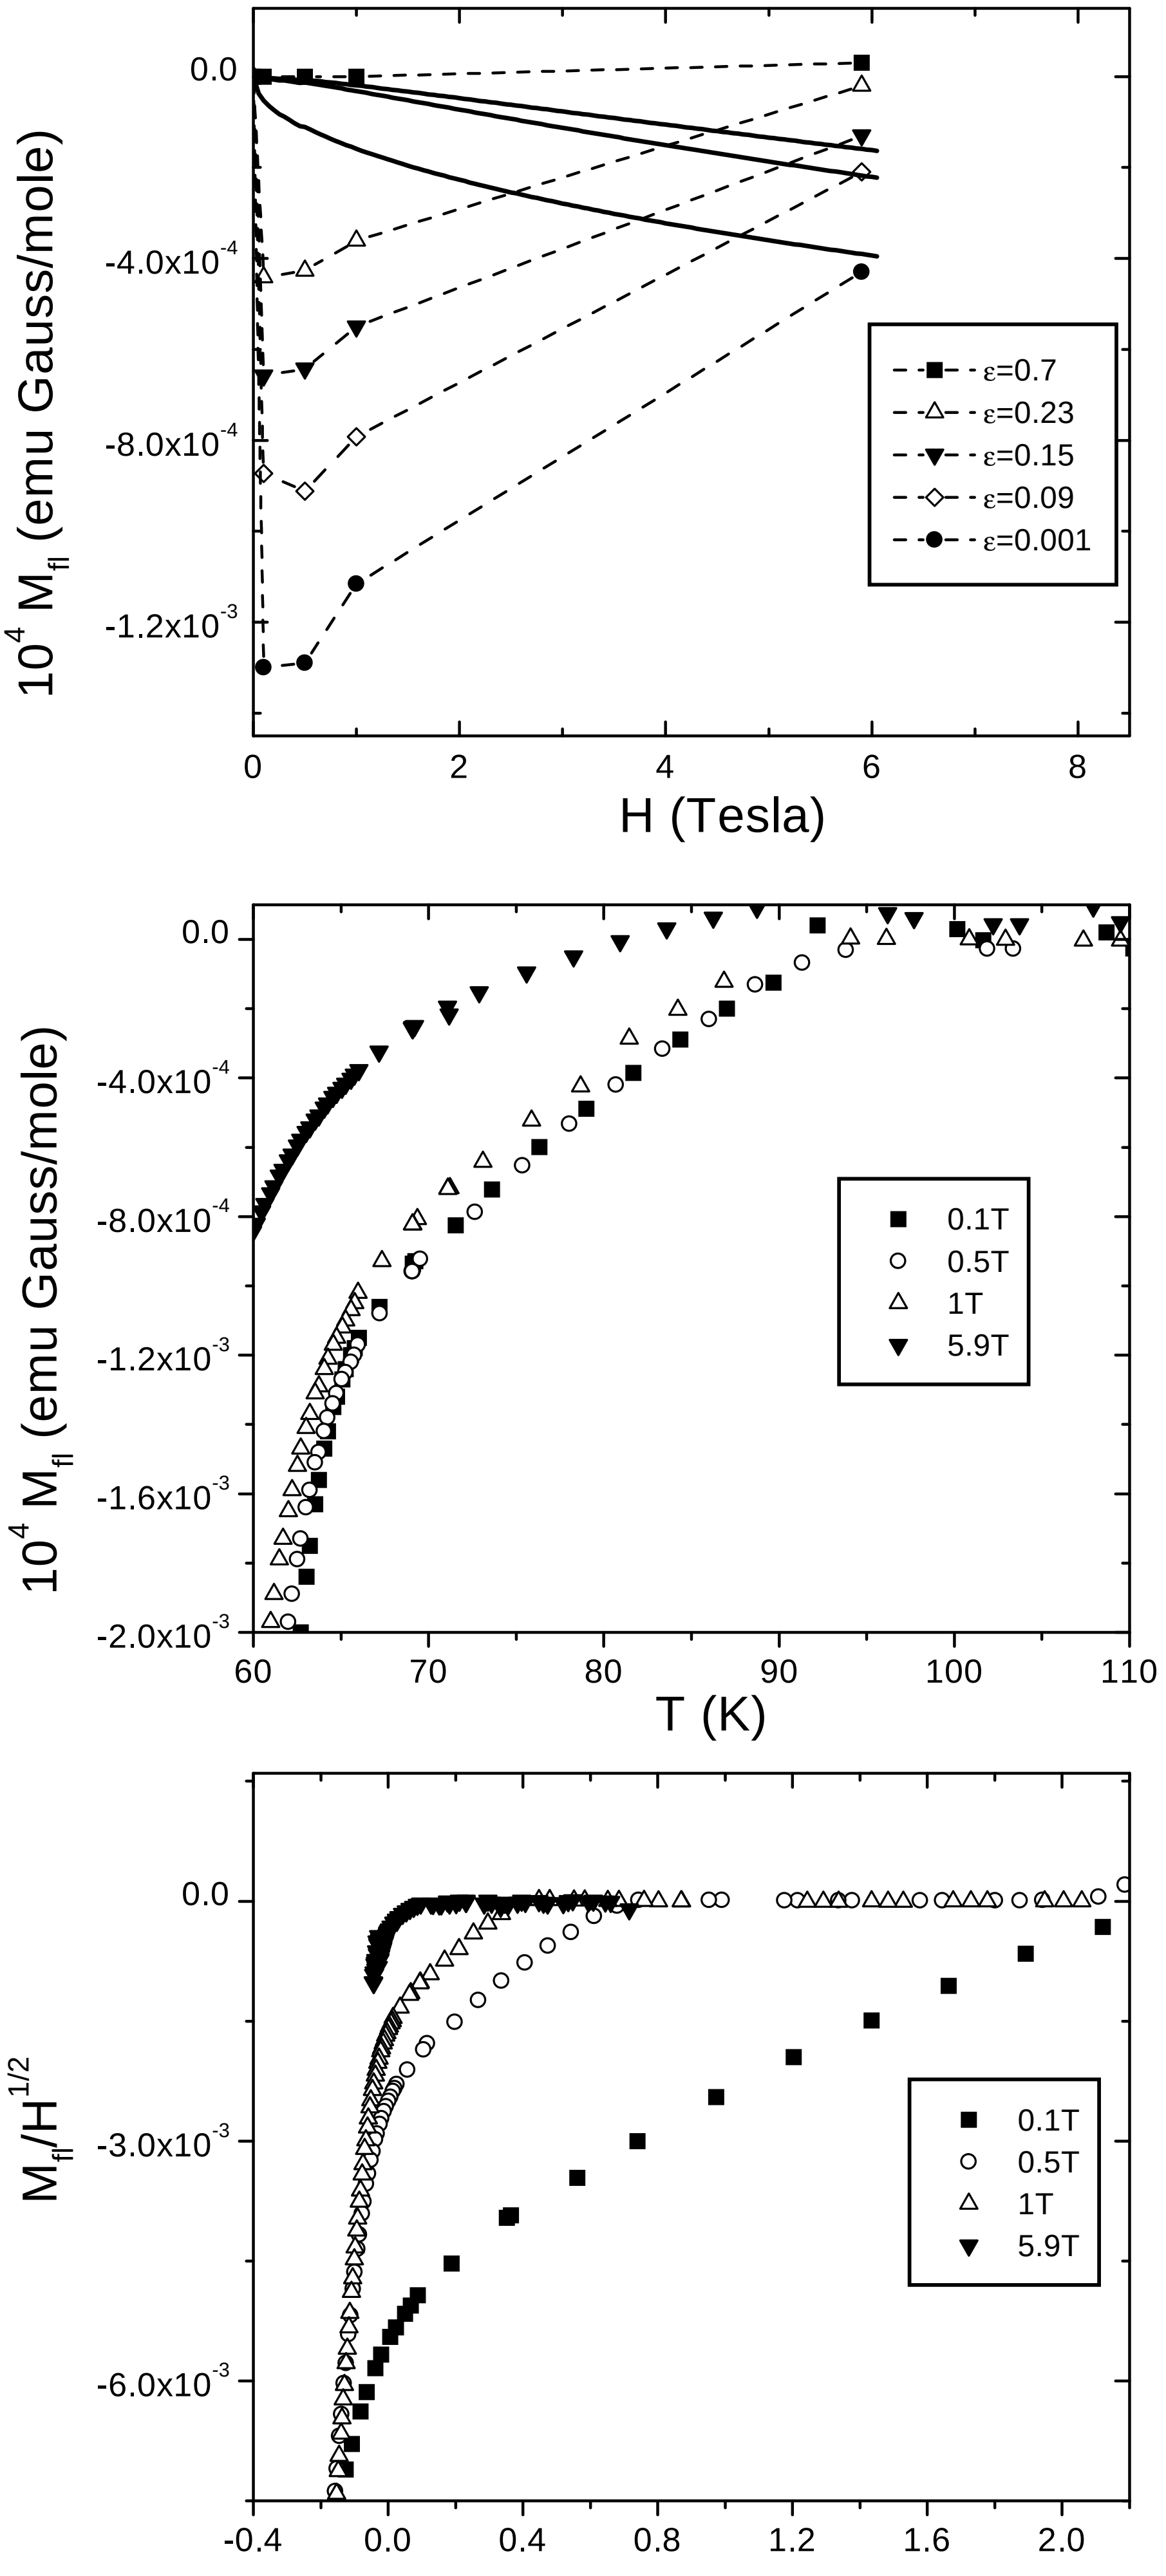
10^4 M_fl (emu Gauss/mole)
0.0
-4.0x10^-4
-8.0x10^-4
-1.2x10^-3
0
2
4
6
8
H (Tesla)
ε=0.7
ε=0.23
ε=0.15
ε=0.09
ε=0.001
10^4 M_fl (emu Gauss/mole)
0.0
-4.0x10^-4
-8.0x10^-4
-1.2x10^-3
-1.6x10^-3
-2.0x10^-3
60
70
80
90
100
110
T (K)
0.1T
0.5T
1T
5.9T
M_fl/H^1/2
0.0
-3.0x10^-3
-6.0x10^-3
-0.4
0.0
0.4
0.8
1.2
1.6
2.0
ε / H^0.747
0.1T
0.5T
1T
5.9T

Fig. 6

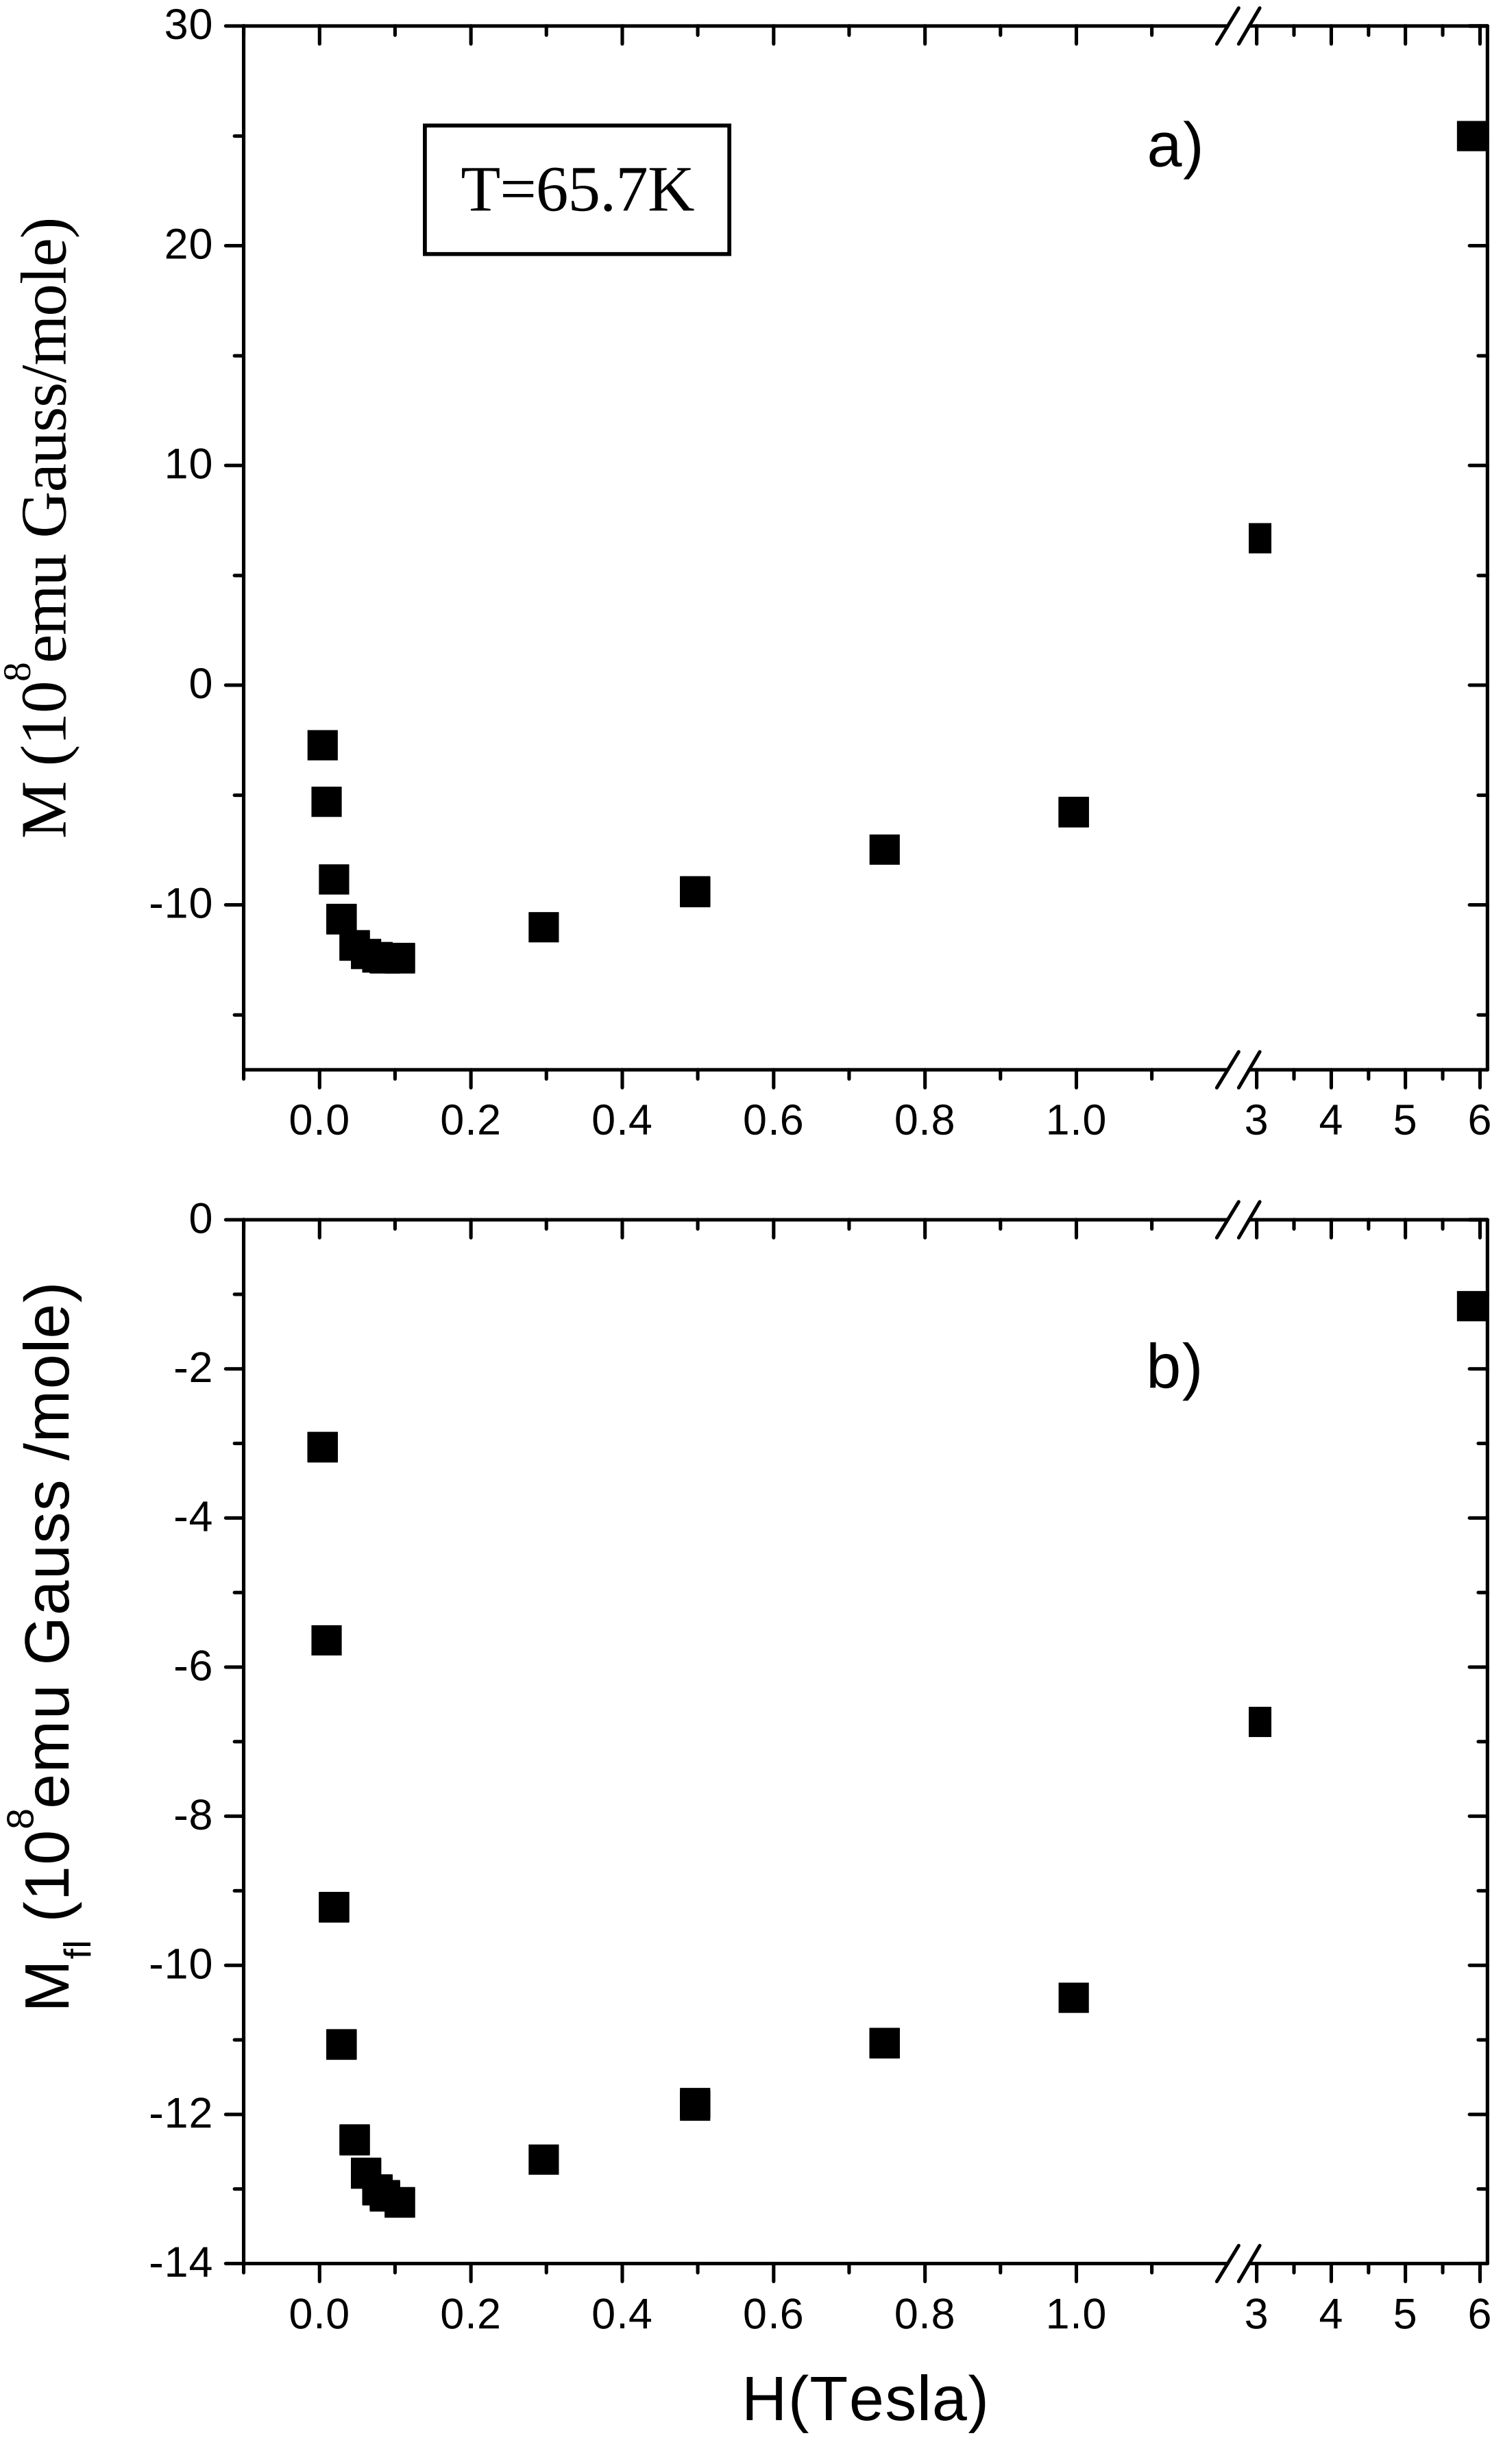
T=65.7K
a)
b)
M (10^8emu Gauss/mole)
M_fl (10^8emu Gauss /mole)
H(Tesla)
30
20
10
0
-10
0
-2
-4
-6
-8
-10
-12
-14
0.0
0.2
0.4
0.6
0.8
1.0
3
4
5
6

Fig. 7